

2021

The Influence of Different Complexing Agents on the Properties of SILAR-Deposited Cobalt Selenide Thin Films

Ho Soonmin

INTI International University, Putra Nilai, 71800, Negeri Sembilan, Malaysia, soonmin.ho@newinti.edu.my

Follow this and additional works at: <https://digitalcommons.aaru.edu.ijtfst>

Recommended Citation

Soonmin, Ho (2021) "The Influence of Different Complexing Agents on the Properties of SILAR-Deposited Cobalt Selenide Thin Films," *International Journal of Thin Film Science and Technology*. Vol. 10 : Iss. 3 , Article 10.

Available at: <https://digitalcommons.aaru.edu.ijtfst/vol10/iss3/10>

This Article is brought to you for free and open access by Arab Journals Platform. It has been accepted for inclusion in International Journal of Thin Film Science and Technology by an authorized editor. The journal is hosted on [Digital Commons](#), an Elsevier platform. For more information, please contact rakan@aar.edu.jo, marah@aar.edu.jo, u.murad@aar.edu.jo.

The Influence of Different Complexing Agents on the Properties of SILAR-Deposited Cobalt Selenide Thin Films

Ho Soonmin*

INTI International University, Putra Nilai, 71800, Negeri Sembilan, Malaysia

Received: 16 Jul. 2021, Revised: 13 Aug. 2021, Accepted: 23 Aug. 2021.

Published online: 1 Sep. 2021.

Abstract: The nanostructured thin films have good physical properties, and could be used in the various applications such as capacitor, photo detector, ultra violet opto electronics, light emitting diode, photonic integrated circuit and solar cell applications. The successive ionic layer adsorption and reaction (SILAR) method is one of the common chemical deposition techniques. This method has many advantages such as the simplest & the cheapest method, and required low temperature deposition process. This is the first time, preparation of cobalt selenide thin films onto soda lime glass slide at room temperature in the presence of various complexing agents (ammonia, triethanolamine and ethylenediaminetetraacetic acid disodium salt). Characterization of thin films was carried by using x-ray diffraction, atomic force microscopy and UV-visible spectrophotometer. AFM analysis showed that the cobalt selenide thin films prepared in the presence of ammonia exhibited uniform and completely covered the entire surface area of substrate. XRD data confirmed that obtained thin films (using ammonia and triethanolamine) were polycrystalline with well-developed phases. Optical properties indicated the band gap values of all films were in the range of 1.8 to 2 eV, suitable to be used in solar cell applications.

Keywords: Thin film, cobalt selenide, solar cell, band gap, absorption.

1 Introduction

The study of the properties of nanostructured thin films has received great attention all over the world. These semiconductor materials were used in different applications including biomedical [1], electro luminescence devices [2], anti-microbial activity, photonic devices, gas sensing [3], optical devices, field emission devices [4], laser devices [5], solar cell [6-9] and electronic devices. Characterization has been done in order to investigate the structural, morphological, optical and compositional of obtained films. These tools including as x-ray diffraction, scanning electron microscopy, energy dispersive x-ray analysis, spectroscopic ellipsometry, Raman Spectroscopy [10], electrochemical impedance spectroscopy, profilometer, Rutherford backscattering spectrometry, scanning tunneling microscopy [11], and atomic force microscopy [12]. Several deposition techniques have been used to produce thin films. These deposition techniques including chemical bath deposition

[13-15], electro deposition [16], evaporation method [17], pulsed laser deposition [18], Spray pyrolysis [19], RF Sputtering [20], molecular beam epitaxy, chemical vapor deposition, sol gel method [21], and SILAR. Among the various deposition techniques, the successive ionic layer adsorption and reaction (SILAR) deposition method is the most commonly used due to simple [22], inexpensive [23], convenient for large area deposition in low temperature [24].

The main goal of this work is to investigate the influence of complexing agent (ammonia, triethanolamine and ethylenediaminetetraacetic acid disodium salt) on the cobalt selenide thin films deposited onto soda lime glass. Characterization of thin films by using X-ray diffraction, atomic force microscopy and UV-visible spectrophotometry was used for the first time.

2 Experimental Details

2.1 Preparation of Thin Films

*Corresponding author E-mail: soonmin.ho@newinti.edu.my

In this experiment, cobalt (II) chloride hexahydrate (acted as a source of Co^{2+} ion) and sodium selenite (supplied Se^{2-} ions) were used without further purification. Thin films were deposited onto soda lime glass slide via SILAR deposition method. The soda lime glass slide was cleaned by acetone, and de-ionized water before use. During the deposition process, the glass substrate immersed in the 0.2 M cationic solution (Co^{2+} ion) containing complexing agent for 35 seconds. After rinsing with de-ionized water for 6 seconds, it was immersed in 0.2 M anionic solution (Se^{2-} ions) containing complexing agent for 35 seconds. Then, rinsing with de-ionized water for 6 seconds again in order to remove the loose material on it. The sodium hydroxide (NaOH) and hydrochloric acid (HCl) were used to adjust pH value. Deposition was carried out at pH 3, at room temperature under different complexing agents such as (0.2 M triethanolamine) TEA, (0.2 M ethylenediaminetetraacetic acid disodium salt) Na_2EDTA and 0.2M ammonia. After the deposition process (after 18 cycles), the films were collected, rinsed by de-ionized water, and finally, put in the oven for 24 hours.

2.2 Characterization of Thin Films

The X-ray diffraction analysis was done to investigate the structure properties of the films. This technique was carried out by using a Malvern Panalytical diffractometer for the 2θ ranging from 10° to 80° with $\text{CuK}\alpha$ ($\lambda = 0.15418$ nm) radiation. The surface morphology, and roughness were analyzed by recording atomic force microscope (AFM) images with Bruker. The mode is Scanasyst peak force tapping. The cantilever is scanasyst-air (material: silicon tip on nitride lever with spring constants 0.4 N/m and resonance frequencies 70 kHz). The surface roughness was studied by on the R_q value. R_q is defined as the root mean square average of height deviation taken from the mean image data plane UV-visible spectrophotometer (Perkin Elmer UV/Vis Lambda 35) was used to investigate the optical properties of films. The thin films were placed across the sample radiation pathway while the cleaned microscope glass slide was put across the reference path. The band gap energy of the films was calculated based on the absorption data.

3 Results and Discussions

Thin film deposition techniques could be divided into two groups, namely physical technique and chemical method. One of the modern chemical deposition methods is called successive ionic layer adsorption and reaction (SILAR) method. SILAR method has many advantages [25]

and can produce film thicknesses in the range of tenths of nanometers to several micrometers [26]. Researcher described that SILAR deposition technique comprised of two important processes [27], namely adsorption of ion onto the substrate and reaction of the adsorbed ion layer will be observed. During the deposition process, several processes could be observed [28, 29] such as dipping into cationic solution, rinsing in de-ionized water, dipping in an ionic solution and rinsing in de-ionized water.

The atomic force microscopy (AFM) measurement was done to study the surface topology of prepared sample. The figure 1 indicated the atomic force microscopy image of SILAR deposited cobalt selenide thin films in the presence of ammonia. This image was measured over $1\ \mu\text{m} \times 1\ \mu\text{m}$ scanning range, indicating three-dimensional view of the sample. Based on the AFM image, cobalt selenide films composed of closely packed uniform crystal. It has dense morphology, compact structure and covers the entire surface area of substrate. The grains (average diameter is $0.05\ \mu\text{m}$) are nearly in spherical in shape and quite small. Film thickness and roughness were $1.1\ \mu\text{m}$ and $0.026\ \mu\text{m}$, respectively. Sapna and co-workers [30] highlighted that the nature of grains has less porous and consisting of small spherical grains. Spherical or grain shaped semiconductor materials are considered as unique properties in thin films. These materials could be used in solar cell applications [31].

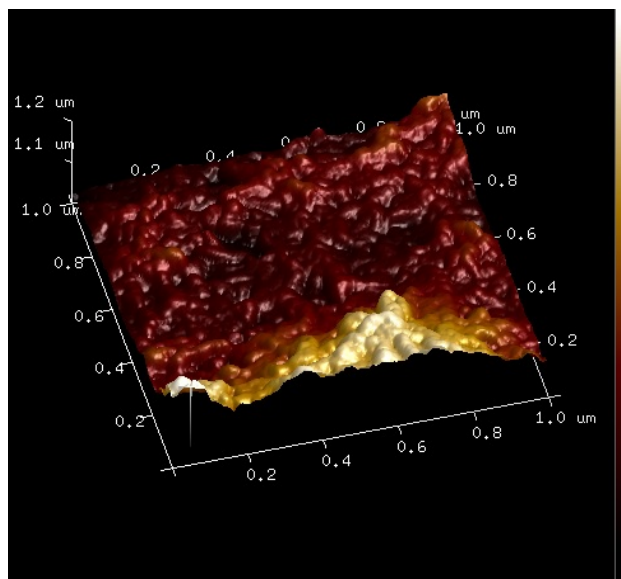


Fig. 1: Three-dimensional AFM view of SILAR deposited cobalt selenide thin films in the presence of ammonia.

Figure 2 indicated the X-ray diffraction (XRD) pattern for the cobalt selenide thin films prepared in the

presence of ammonia. Based on the figure, the XRD pattern showed several diffraction peaks at $2\theta=24.5^\circ$, 28.7° , 33.9° and 37.8° , which can be indexed as reflection from the (022), (113), (004) and (133) plane of the cubic structure Co_9Se_8 compound. Other researchers have reported similar findings (cubic cobalt selenide structure) in the literature [32, 33]. The obtained X-ray diffraction pattern was well matched with the standard Joint Committee on Powder Diffraction Standards (JCPDS) (Reference code: 98-004-4857) as indicated in Table 1. According to the JCPDS data, lattice parameter values are $a=b=c=10.431 \text{ \AA}$. The crystal system, space group and space group number were cubic, Fm-3m and 225, respectively.

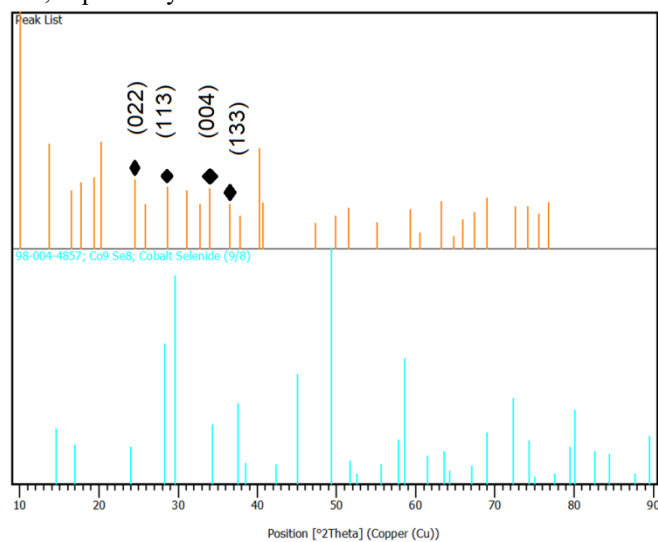


Fig. 2: X-ray diffraction pattern for the cobalt selenide thin films prepared in the presence of ammonia.

Table 1: Comparison of observed d-spacing values with standard d-spacing values of cobalt selenide thin films by using ammonia.

2θ ($^\circ$)	hkl	Observed d-spacing values (\AA)	Standard d-spacing values (\AA)
24.5	022	3.6	3.6
28.7	113	3.1	3.1
33.9	004	2.6	2.6
37.8	133	2.4	2.4

Figure 3 indicates absorbance spectrum (in the wavelength of 300 to 1000 nm) of cobalt selenide thin films prepared in the presence of ammonia. Generally, the obtained sample showed high absorption in the visible range, which make these materials possible to use in the photo electrochemical cell and solar cells. Following that, absorbance reduces with the increasing of wavelength. A similar tendency was also seen by other researchers [34, 35]. The band gap was

calculated based on the Stern equation which recommended by many researchers [36-42].

$$A = \frac{[k(h\nu - E_g)]^{n/2}}{h\nu} \text{ [equation 1]}$$

where ν is the frequency, h is the Planck's constant, k equals a constant while n carries the value of either 1 or 4. The n value is 1 for a direct gap material and 4 for indirect gap material. The plot of $(Ah\nu)^2$ against $h\nu$ is indicated in figure 4. Extrapolation of the linear portion of the curve to $(Ah\nu)^2=0$ produce the band gap energy. The band gap was calculated to be 1.8 eV. These semiconductor materials could be used in solar cell applications because of direct band gap between 1 to 2 eV [43, 44]. Other scientist groups have reported similar band gap values (Table 2) for the cobalt selenide thin films prepared under various deposition techniques including chemical bath deposition, electro deposition, magnetron sputtering method and mechano chemical method.

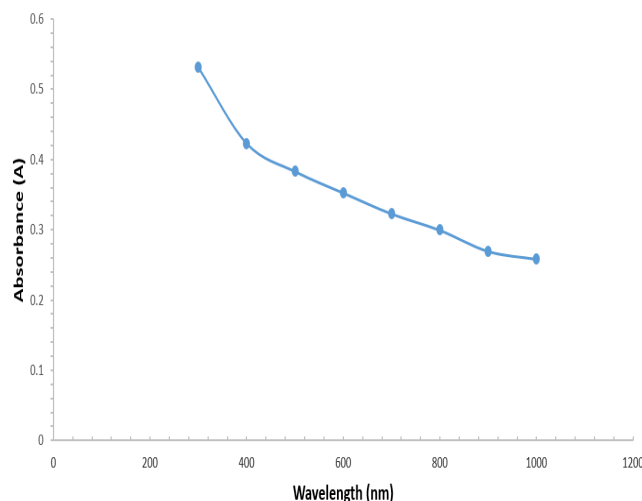


Fig. 3: Optical absorbance spectrum of cobalt selenide thin films prepared in the presence of ammonia.

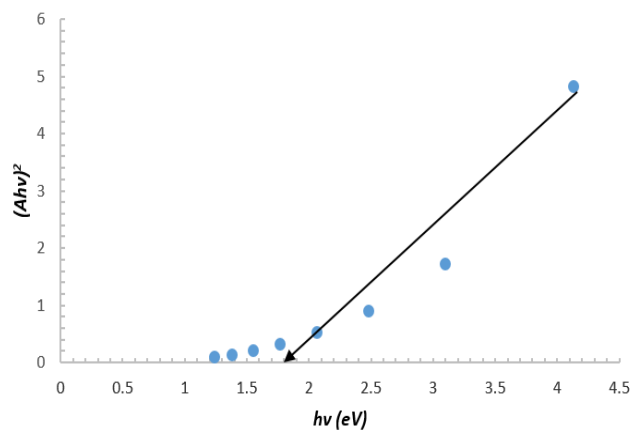


Fig. 4: Plot of $(Ah\nu)^2$ against $(h\nu)$ of cobalt selenide thin films prepared in the presence of ammonia.

Table 2: Band gap energy of cobalt selenide thin films prepared under different deposition techniques.

Remarks	Band gap value (eV)
Thin films were produced onto glass substrate by using chemical bath deposition method in the presence of ammonia, cobalt (II) acetate and sodium selenosulphite as reported by Ghobadi and co-workers [45].	1.8 to 3.6
Thin films were synthesized onto tin oxide glass substrate via electro deposition technique in the presence of H_2SeO_3 and $Co(CH_3COO)_2$ solutions as described by Liu and co-workers [46].	1.53
Thin films were prepared onto non-conducting micro glass slide through chemical bath deposition method, in the presence of cobalt nitrate, ammonia and sodium selenosulphate as highlighted by Muddsar and co-workers [47].	1.7
Thin films were produced using magnetron sputtering method as pointed out by Zhu and co-workers [48].	1.53
Thin films were synthesized onto tin oxide coated glass by using electrodeposition method as concluded by Wang and co-workers [49].	1.53
Thin films were grown using the mechanochemical method as reported by Nina and co-workers [50].	1.7

The figure 5 exhibited the 3-dimensional atomic force microscopy image ($1 \mu m \times 1 \mu m$ scanning range) of SILAR deposited cobalt selenide thin films with the addition of triethanolamine (TEA). The AFM image showed the prepared films have non-uniform (0.03 to 0.1 μm) surface and cover the entire surface area of substrate. The formation of films modeled as mixture of small and big nano-grains. Film thickness and roughness were about 1.2 μm and 0.0245 μm , respectively. The influence of triethanolamine on the surface roughness and morphological properties of films have been studied by many researchers. Manikandan and co-workers [51] have reported that FeS films prepared by using 0.15 M TEA showed excellent structure. Preettha and co-workers [52] have highlighted that densely packed with bigger grains for the films prepared using TEA. Kishorkumar and co-workers [53] have pointed out that several obvious differences in morphology (nanoflake, nano sphere and

nanocoral-like morphology) can be observed after addition of TEA.

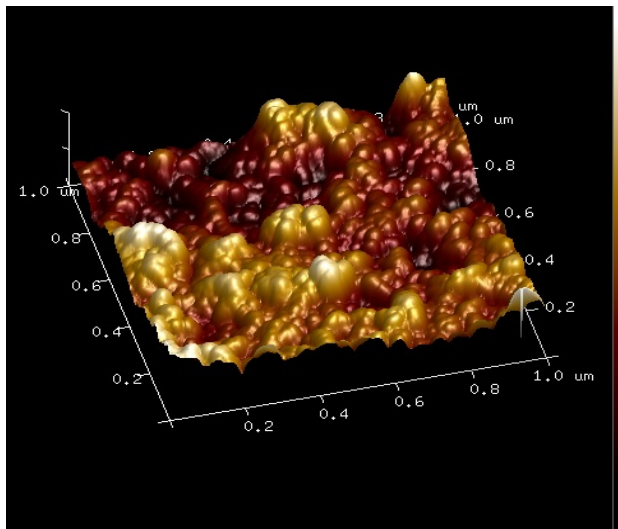


Fig.5: Three-dimensional AFM view of SILAR deposited cobalt selenide thin films in the presence of TEA.

Structural studies confirm that the films prepared using triethanolamine were polycrystalline in nature (Figure 6). Several diffraction peaks such as (002), (022), (113), (222), (135), (006), (246), (355), (337) and (066) could be observed. The obtained d-spacing values matched well with JCPDS data (Reference: 98-004-4857) as shown in Table 3. The number of diffraction peaks increased to ten peaks if compared to films prepared using ammonia (4 peaks), indicating more favourable condition for the formation of cobalt selenide (Co_9Se_8) thin films. The TEA complex resulted in better crystallinity as reported by other researchers [54-56].

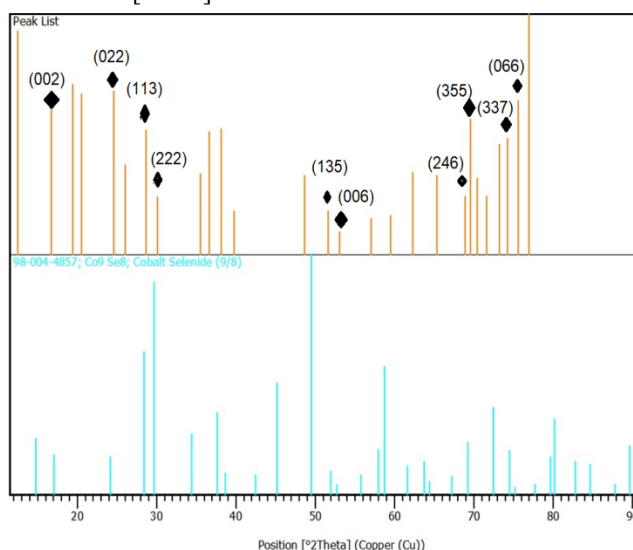


Fig.6: X-ray diffraction pattern for the cobalt selenide thin films prepared in the presence of TEA.

Table 3: Comparison of observed d-spacing values with standard d-spacing values of cobalt selenide thin films by using TEA.

2θ ($^\circ$)	hkl	Observed d-spacing values (Å)	Standard d-spacing values (Å)
16.7	002	5.3	5.2
24.5	022	3.6	3.7
28.6	113	3.1	3.1
30.1	222	3.0	3.0
51.7	135	1.8	1.8
53.1	006	1.7	1.7
68.9	246	1.4	1.4
69.6	355	1.3	1.3
74.2	337	1.28	1.27
75.6	066	1.25	1.23

The optical properties of cobalt selenide thin films were studied and the absorption spectrum was displayed in Figure 7 (in the wavelength of 300 to 1000 nm). The results confirmed that high absorption in the visible range, indicating these films could be used in solar cell applications. The plot of $(Ah\nu)^2$ against $h\nu$ is indicated in figure 8. Band gap could be measured when extrapolation of the linear portion of the curve to $(Ah\nu)^2=0$. The band gap was about 1.9 eV. The band gap has vital importance in photovoltaic related applications. The thin films have band gap of 1 to 2 eV are most suitable for solar cell applications [57-59].

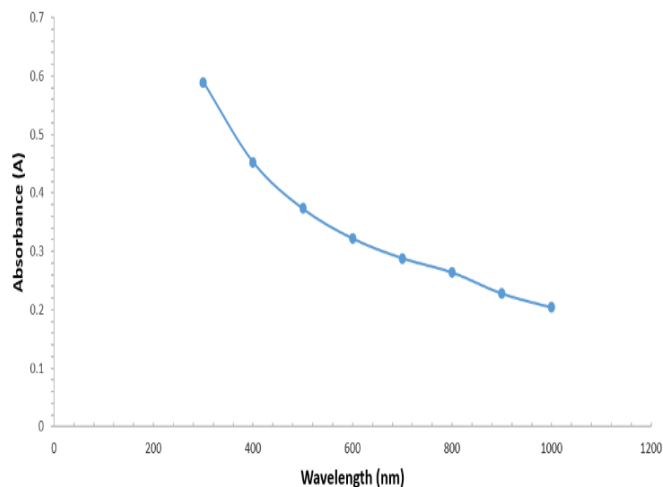


Fig. 7: Optical absorbance spectrum of cobalt selenide thin films prepared in the presence of TEA.

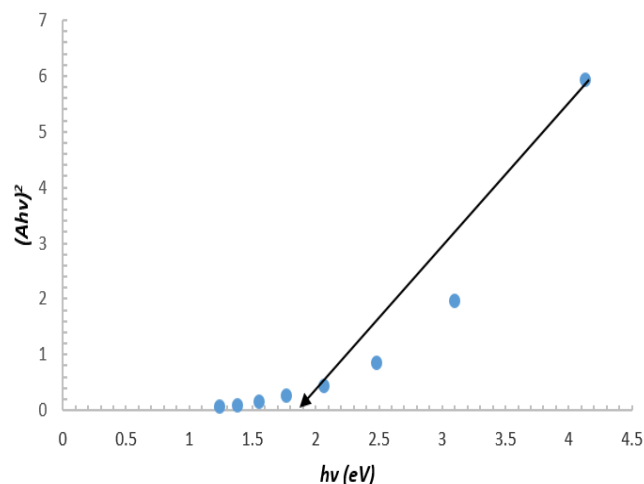


Fig. 8: Plot of $(Ah\nu)^2$ against $h\nu$ of cobalt selenide thin films prepared in the presence of TEA.

The AFM measurements were scanned in $1\ \mu\text{m} \times 1\ \mu\text{m}$ area. In the AFM image, several large grains (average diameter is $0.05\ \mu\text{m}$) were clearly apparent in the surface of substrate (figure 9). Non-uniform grain size could be observed for the films prepared using Na_2EDTA (Ethylenediaminetetraacetic acid disodium salt), indicating this complexing agent is not favorable. The film thickness and surface roughness were about $1.5\ \mu\text{m}$ and $0.0046\ \mu\text{m}$, respectively.

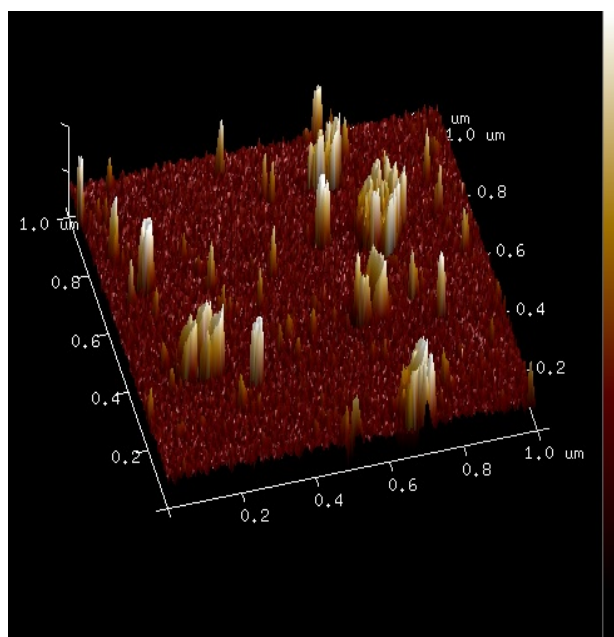


Fig.9: Three-dimensional AFM view of SILAR deposited cobalt selenide thin films in the presence of Na_2EDTA .

The XRD results reveal that the cobalt selenide (Co_9Se_8) films prepared by addition Na_2EDTA exhibited poor crystallinity. In this XRD analysis, prepared sample

indicated single diffraction peak (figure 10), attributed to (111) plane. The observed d-spacing value was matched [Table 4] with JCPDS data [Reference: 98-004-4857].

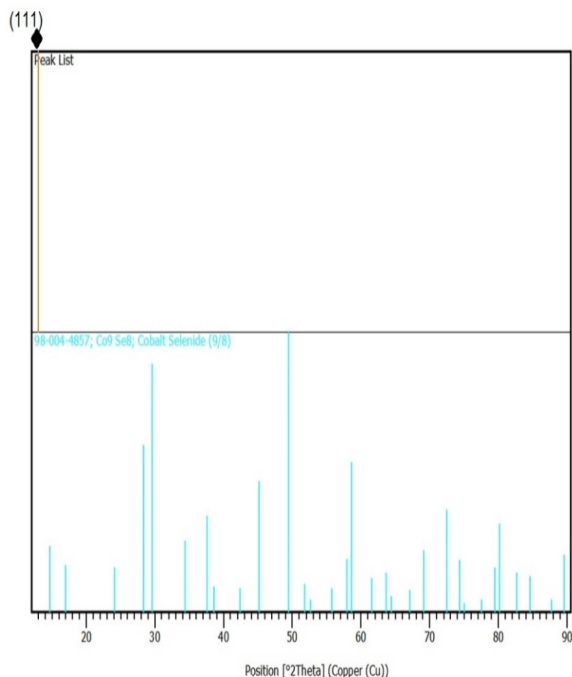


Fig.10: X-ray diffraction pattern for the cobalt selenide thin films prepared in the presence of Na_2EDTA .

Table 4: Comparison of observed d-spacing value with standard d-spacing value of cobalt selenide thin films by using Na_2EDTA .

2θ ($^\circ$)	hkl	Observed d-spacing value (\AA)	Standard d-spacing value (\AA)
13.03	111	6.7	6.0

The optical absorption spectrum was recorded in the wavelength range between 300 to 1000 nm using UV-visible spectrophotometer. From the figure 11, noted that the highest absorbance value could be observed in the short wavelength. Similar results have been described in binary, ternary and quaternary thin films [60,61]. However, absorbance reduces with the increase in the wavelength. In the near infra-red region, the curves reveal a very low absorption of energy [62]. The band gap is 2 eV as shown in figure 12.

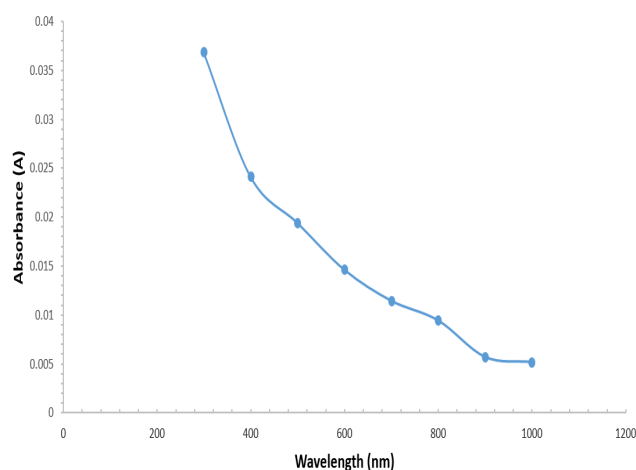


Fig.11: Optical absorbance spectrum of cobalt selenide thin films prepared in the presence of Na_2EDTA .

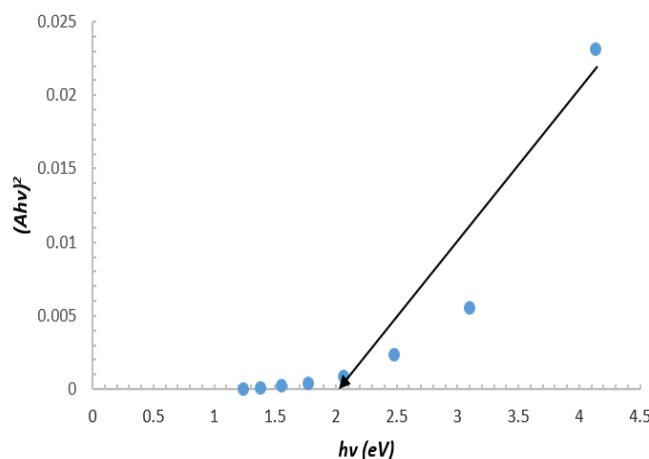


Fig.12: Plot of $(Ah\nu)^2$ against $(h\nu)$ of cobalt selenide thin films prepared in the presence of Na_2EDTA .

The role of complexing agent in synthesis of thin films has been reported by many researchers. Several types of complexing agents such as hydrazine hydrate, triethylamin, nitrilotriacetic acid, glycine, tri-sodium citrate and tartaric acid were used during the deposition of thin films. Thin films prepared in the presence of complexing agent reduced the deposition rate due to higher complexation, improved the quality of thin films. Table 5 indicated that the obtained experimental results strongly depended on the amount of complexing agent and the nature of complexing agent.

Table 5: Thin films have been prepared by using various different complexing agents.

Thin films	Highlighted results	Complexing agent
zinc selenide	<ul style="list-style-type: none"> • Deposition was carried out in alkaline conditions, low temperature via chemical bath deposition method as reported by Hile and co-workers [63]. • Morphological studies revealed that spherical grain changed to nano-flakes when the complexing agent volume was increased (5 to 35 mL). 	hydrazine hydrate
Lead sulphide	<ul style="list-style-type: none"> • Chemical bath deposition method was used to synthesis thin films onto glass slide as highlighted by Fekadu and Dejene [64]. • The major diffraction peak could be observed in the (111) plane, higher intensity of the diffraction peaks could be seen with increasing the concentration of complexing agent. 	triethylamin
Ho doped (Cd-Ag)S films	<ul style="list-style-type: none"> • The growth thin films at room temperature onto glass slide through chemical bath deposition method as described by Yadu and co-workers [65]. • Ho-doped (Cd-Ag)S films have smaller particle size if compared to as-deposited films. Also, these films showed globular ball type and flakes type structure. 	Ethylenediamine tetraacetic, triethanolamine
ZnS	<ul style="list-style-type: none"> • The complexing agents that produce stable complexes with the Zn^{2+} ions in the reaction bath. S^{2-} has been released from the decomposition of thiourea in the presence of hydroxide as pointed out by Kazi and co-workers [66]. • A high concentration of the complexing agent, causes to a heterojunction reaction on the substrate surface. 	Tri-sodium citrate and tartaric acid
PbS	<ul style="list-style-type: none"> • Thin films were prepared using chemical bath deposition method as explained by Chalapathi and co-workers [67]. • The films prepared in the presence of complexing agent showed large grained with improved hole mobilities. 	ethylenediamine tetraacetic acid
SnS	<ul style="list-style-type: none"> • Chemical bath deposition method was used to produce thin films as reported by Gaitan and co-workers [68]. • The films prepared using complexing agent formed thicker films, better grain connectivity, and the formation of cubic SnS. 	nitrilotriacetic acid

Pr doped CuInS ₂ film	<ul style="list-style-type: none"> • Thin films were synthesized using chemical bath deposition at 80 °C as highlighted by Sengupta and Pateria [69]. • The obtained films indicated high transmittance, low reflectance found in the visible region. Also, results exhibited high photocurrent is found, and good photosensitivity is observed in films. 	triethanolamine
Cu ₂ ZnSnS ₄ films	<ul style="list-style-type: none"> • Electro deposition was used to prepare thin films as pointed out by Demir [70]. • Deposition was carried out onto indium tin oxide glass, pH 5, deposition time (2700 seconds), and deposition potential of -1.05 V. • Formation of stoichiometric kesterite structure as indicated in XRD analysis. 	Trisodium citrate
PbS	<ul style="list-style-type: none"> • Thin films have been synthesized onto glass slide in alkaline conditions, using chemical bath deposition method as concluded by Yesica and Luis [71]. • The films showed unique properties such as highly compact and adherent films, pyramid-like particles, cubic structure. 	glycine
Cu ₂ ZnSnS ₄ films	<ul style="list-style-type: none"> • Solvothermal method was used to produce thin films as described by Hadeethi and co-workers [72]. • The films prepared showed single phase nanocrystals, high purity and excellent crystallinity. 	glycine
ZnS	<ul style="list-style-type: none"> • Chemical spray pyrolysis method was used to produce thin films as pointed out by Offor and co-workers [73]. • Morphology studies revealed that nano dot-like and nano rod-like crystals were observed with increasing molar concentration (complexing agent) 	trisodium citrate

5 Conclusions

The cobalt selenide thin films were deposited onto soda lime glass by using SILAR method under various complexing agents. AFM studies demonstrated that surface morphology was markedly affected by the nature of the complexing agents. XRD data confirmed that obtained thin films (using ammonia and triethanolamine) were polycrystalline with well-developed phases. Experimental results confirmed that complexing agent played an important role in the formation of the thin films.

Acknowledgements

Research work funded by INTI International University (INTI Internal Research Grant INTI –CAE-01-01-2018).

References

- [1] B. Marcin, S. Marek, L. Vira, Z. Boguslaw, W. Simka. Atomic layer deposited ZnO films on stainless steel for biomedical applications, *Archives Civil and Mechanical Engineering*, 2021; <https://doi.org/10.1007/s43452-020-00148-5>.
- [2] D. Hile, H. Swart, F. Koao, B. Pawade, E. Kroon. Synthesis and characterization of europium doped zinc selenide thin films prepared by photo-assisted chemical bath technique for luminescence application, *Materials Chemistry and Physics*, 2021; <https://doi.org/10.1016/j.matchemphys.2021.124303>.
- [3] T. Gupta, P. Chauhan. Impact of N⁺ ion implantation on the properties of ZnSe thin films, *Journal of Materials Science: Materials in Electronics*, **32**, 6185-6198, 2021..
- [4] Z. Zeng, S. Xue, S. Wu, X. Gan, W. Han. Synthesis, field emission and optical properties of ZnSe nanobelts, nanorods and nanocones by hydrothermal method, *Materials Science in Semiconductor Processing*, **31**, 189-194, 2015.
- [5] M. Taj, M. Farhan, M. Arshad, A. Shah. Synthesis of thermally evaporated ZnSe thin film at room temperature, *Thin Solid Films*, **519**, 5971-5977, 2011.
- [6] S.M. Ho. Chemical bath deposited lead sulphide thin films: Preparation and characterization, *World of Mechanics*, 1-6, 2014.
- [7] S. Atan, K. Anuar, S.M. Ho, W. Tan, N. Saravanan. Effect of deposition period and pH on chemical bath deposited Cu₄SnS₄ thin films, *Philippine Journal of Science*, **138**, 161-168, 2009.
- [8] B. Tom, G. Zoppi, B. Leon, D. Major. Incorporation of CdSe layers into CdTe thin film solar cells, *Solar Energy Materials and Solar Cells*, **180**,196-204, 2018.
- [9] M. Shanmugam, S.M. Ho, J. Markna, M. Mordiya. Review on dye sensitized solar cells based on polymer electrolytes, *International Journal of Engineering & Technology*, **7**,3001-3006, 2018.
- [10] S.M. Ho, M. Othman, M. Adam, K. Mohanraj. A short review on Raman studies of metal chalcogenide semiconductor thin films, *Asian Journal of Chemistry*, **33**,1481-1487, 2021.
- [11] E. Nogales, B. Mendez, J. Piqueras, R. Plugaru. Scanning tunneling microscopy and spectroscopy of nanocrystalline silicon films, *Semiconductor Science and Technology*, 2001; <https://doi.org/10.1088/0268-1242/16/9/309>.
- [12] H. Soonmin. Metal selenide semiconductor thin films: a review, *International Journal of ChemTech Research*, **9** , 390-395, 2016.
- [13] K. Haleh, E. Parisa. Structural Properties of Indium Sulfide Thin Films Produced by CBD Method at Different Deposition Temperature, *Indian Journal of Science and Technology*, 2015; DOI: [10.17485/ijst/2015/v8i35/85916](https://doi.org/10.17485/ijst/2015/v8i35/85916).
- [14] S.M. Ho. Chalcogenide thin films prepared using chemical bath deposition method, *Research Journal of Applied Sciences, Engineering and Technology*, **11** (2015) 1058-1065.
- [15] S.M. Ho. Preparation and characterization of nickel oxide thin films: a review, *International Journal of Applied Chemistry*, **12** (2016) 87-93.
- [16] K. Anuar, S.M. Ho, K. Noraini, N. Saravanan. XRD and AFM studies of ZnS thin films produced by electrodeposition method, *Arabian Journal of Chemistry*, **3**, 243-249, 2010.
- [17] M. Abdeljalil, A. Taher, R. Shaaban. Applying optical Swanepoels model to access the effect of UV irradiated time on optical properties of ZnSe thick film, *International Journal of Thin Film Science and Technology*, **10**, 137-142, 2021.
- [18] I. Najm, M. Kadhim, A. Ali. Investigation the CuS thin film prepared by pulsed laser deposition, *Materials Today*, **42**, 2609-2615, 2021.
- [19] G. Evgeny, D. Savin, T. Tatyana, U. Dmitry, K. Sergey. Spray pyrolysis deposited Cr and In doped CdS films for laser application, *Optical Materials*, 2021; <https://doi.org/10.1016/j.optmat.2021.111153>.
- [20] G. Kapil, S. Kumar. Effect of Post Annealing on the Structural Properties of Vanadium Oxide Thin Film Deposited by RF Sputtering, *Indian Journal of Science and Technology*, 2017; DOI: [10.17485/ijst/2017/v10i42/115790](https://doi.org/10.17485/ijst/2017/v10i42/115790).
- [21] A. Hamed. Synthesis and characterization of BaSrTiO₃ perovskite thin films prepared by sol gel technique, *International Journal of Thin Film Science and Technology*, **10**, 95-100, 2021.
- [22] O. Balayeva, M. Eyvazova, M. Mirsultanova. Role of temperature in the growth and formation of Cd_{0.9}Zn_{0.1}S/PVA nanocomposites through SILAR method, *Materials Research Bulletin*, 2021; <https://doi.org/10.1016/j.materresbull.2020.111162>.
- [23] S. Araz, F. Javid, P. Givi, A. Yashar. Formation of CdS/ZnS nanoparticles in polymer matrix by SILAR method: Experiments and exploring its optical properties with DDA calculations, *Optik*, 2021; <https://doi.org/10.1016/j.ijleo.2021.166958>.
- [24] K. Kumar, B. Balaji, P. Gnana, E. Reon. Investigations on SILAR coated CZTS thin films for solar cells applications, *Phase Transitions*, 2021; <https://doi.org/10.1080/01411594.2021.1939874>.
- [25] M. Anbazhagan, V. Siva, S. Abdul, A. Sultan. Optimization of adsorption and reaction time of SILAR deposited Cu₂ZnSnS₄ thin films: Structural, optical and electrochemical performance, *Journal of Alloys and Compounds*, 2021; <https://doi.org/10.1016/j.jallcom.2020.158055>.
- [26] S. Yosita, F. Liu, Q. Shen, Y. Witoon. Synthesis of Pb-doped CdS quantum dot using SILAR method on mesoporous TiO₂ layer, *Journal of Physics: Conference Series*, 2021; <https://doi.org/10.1088/1742-6596/1719/1/012063>.
- [27] T. Fowodu, Q. Adeniji, K. Odunaike. The growth and opto-electrical characterization of SILAR grown iron copper sulphide (FeCuS) ternary thin films, *International Journal of Thin Films Science and Technology*, **10**, 20217-11, 2021.
- [28] A. Bronusiene, A. Popov, I. Ancutiene. Effect of ascorbic acid on the properties of tin sulfide films for supercapacitor application, *Surfaces and Interfaces*, 2021 <https://doi.org/10.1016/j.surfin.2021.101275>.
- [29] O. Kola, A. Adeniji, A. Sheu, A. Alabi. Effect of Different Silar Cycle on Chemically Deposited Zinc Copper Sulphide (ZnCuS), *International Journal of Thin Films Science and Technology*, **10** 117-120, 2021.

- [30] P. Sapna, K. Preetha. Effect of pH on SILAR deposited CTS thin films. IOP Conference Series: Materials Science and Engineering, 2019; doi:10.1088/1757-899X/577/1/012086.
- [31] Spherical or grain-shaped semiconductor element for use in solar cells and method for producing the same; method for producing a solar cell comprising said semiconductor element and solar cell. <https://patents.google.com/patent/US20070089782>. [Accessed on 18 July 2021]
- [32] M. Gaur, P. Hankare, S. Mulla, M. Bhuse. Morphological and optical properties of mixed cadmium cobalt selenide thin film synthesized by chemical bath deposition method for photo electrochemical applications, Journal of Materials Science: Materials in Electronics, 27,7603-7608, 2016.
- [33] A. Panneerselvam, C. Nguyen, J. Waters, A. Malik, O. Paul. Ligand influence on the formation of P/Se semiconductor materials from metal organic complexes, Dalton Transactions, 2008; <https://doi.org/10.1039/B802012D>.
- [34] K. Pathan, H. Siddiquee, S. Alam, O. Islam. Structural and optical characterization of CdS and CdHgTe thin films for the fabrication of CdHgTe/CdS structure, Journal of Materials Science: Materials in Electronics, 24, 745-751, 2013.
- [35] M. Khalaf, M. Baha, I. Ausama, A. Anwar. Influence of nanocrystalline size on optical band gap in CdSe thin films prepared by DC sputtering, Photonics and Nanostructures-Fundamentals and Applications., 18, 59-66, 2016.
- [36] S. Teo, Z. Zainal, W. Tan, H. Imad. Potentiostatic deposition of copper indium disulfide thin films: effects of cathodic potentials on the optical and photo electro chemical properties, The Malaysian Journal of Analytical Sciences., 12, 600-608, 2008.
- [37] H. Sachin, K. Patil, S. Lad, M. Bhagwat. Optical study of ZnS solid thin film prepared by spray pyrolysis technique, Archives of Physics Research., 4,7-11, 2013.
- [38] G. Jigi, T. Abza, A. Girma. Synthesis and characterization of aluminium doped zinc sulfide (Al:ZnS) thin films by chemical bath deposition techniques, Journal of Applied Biotechnology and Bioengineering., 8, 55-58, 2021.
- [39] C. Kumarage, P. Wijesundera, N. Kaur, D. Zappa, A. Jayalath. A comparative assessment: chemical bath deposited and electrodeposited CdS films, International Journal of Electroactive Materials, 7,1-6, 2019.
- [40] A. Kassim, S.M. Ho, H. Abdul, W.T. Tan, N. Saravanan. Deposition and characterization of Cu₄SnS₄ thin films by chemical bath deposition method, Macedonian Journal of Chemistry and Chemical Engineering., 29, 97-103, 2010.
- [41] K. Anuar, S.M. Ho, M. Yazid. UV-visible studies of chemical bath deposited NiSe thin films, International Journal of Chemical Research., 3, 21-26, 2011.
- [42] N. Saravanan, S.M. Ho, A. Kassim, W. Tan, D. Teo. Chemical bath deposition of nickel sulphide (Ni₃S₂) thin films, Leonardo Journal of Sciences., 16, 1-12, 2010.
- [43] S.M. Ho. Power conversion efficiency in thin film solar cell: a review, International Journal of Chemical Sciences, 14, 143-151, 2016.
- [44] T. Sinha, L. Verma, K. Ayush. Variations in photovoltaic parameters of CdTe/CdS thin film solar cells by changing the substrate for the deposition of CdS window layer, Applied physics A, 2020; <https://doi.org/10.1007/s00339-020-04058-4>.
- [45] N. Ghobadi, F. Hafezi, S. Naderi, M. Habibi. Microstructure and optical band gap of cobalt selenide nanofilms, Semiconductors., 53 1751-1758, 2019.
- [46] F. Liu, B. Wang, Y. Lai, Z. Zhang, Y. Liu. Electrodeposition of cobalt selenide thin films, Journal of The Electrochemical Society, 2010; <https://doi.org/10.1149/1.3468675>.
- [47] G. Muddsar, P. Hankare, G. Kalyanrao, M. Imtiaz, V. Bhuse. Morphological and optoelectronic studies on poly crystalline leaf like cobalt selenide thin film synthesized using chemical bath deposition technique, New Journal of Chemistry, 2014; DOI: [10.1039/C3NJ00924F](https://doi.org/10.1039/C3NJ00924F).
- [48] L. Zhu, A. Lam, D. Susac, M. Teo, R. Parsons. Structure of sputtered Co-Se thin films prepared for an application in catalysis, Journal of Solid State Chemistry., 179, 3942-3948, 2006..
- [49] B. Wang, Y. Liu, L. Jie, Y. Lai, Z. Zhang. Preparation and characterization of Co-Se thin films by electro deposition, Journal of Inorganic Materials, 2011; DOI: 10.3724/SP.J.1077.2011.00403.
- [50] D. Nina, A. Anna, A. Marcela. Mechanochemically synthesized cobalt monoselenide: structural characterization and optical properties, Applied Physics A, 2017; <https://doi.org/10.1007/s00339-017-0785-9>.
- [51] K. Manikandan, P. Mani, S. Dilip, S. Valli, H. Inbaraj. Effect of complexing agent TEA: The structural, morphological, topographical and optical properties of Fe₃S₄ nano thin films deposited by SILAR technique, Applied Surface Science., 288, 76-82, 2014.
- [52] K. Preetha., K. Deepa, C. Dhanya, T. Remadevi. Role of complexing agents on chemical bath deposited PbS thin film characterization, IOP Conference Series: Materials Science and Engineering, 2015; <https://doi.org/10.1088/1757-899X/73/1/012086>.
- [53] V. Kishorkumar, S. Sawanta, B. Nita, R. Rohini. Development of nanocoral-like Cd(SSe) thin films via arrested precipitation technique and their application, New Journal of Chemistry., 38, 5964-5974, 2014.
- [54] H. Cavusoglu, R. Aydin. Complexing agent triethanolamine mediated synthesis of nanocrystalline CuO thin films at room temperature via SILAR technique, Superlattices and Microstructures., 128 , 37-47, 2019.
- [55] S. Patil, A. Singh. Effect of complexing agent on the photo electrochemical properties of bath deposited CdS thin films, Applied Surface Science., 256 , 2884-2889, 2010.
- [56] A. Okereke, A. Ezenwa, A. Ekpunobi. Effect of complexing agent (TEA) on chemically deposited silver selenide thin films, International Journal of Science and Technology, 2, 155-158, 2012.
- [57] G. Jarosz, M. Rafal, S. Ryszard. Effect of band gap on power conversion efficiency of single-junction semiconductor photovoltaic cells under white light phosphor-based LED illumination, Materials Science in Semiconductor Processing, 2020; <https://doi.org/10.1016/j.mssp.2019.104812>.
- [58] K. Teodor, S. Singh, M. Bishop, M. Oki. Ultrathin high band gap solar cells with improved efficiencies from the world oldest photovoltaic material, Nature Communications, 2017; <https://doi.org/10.1038/s41467-017-00582-9>.
- [59] Z. Xiao, Y. Zhou, H. Hideo, T. Kamiya, P. Nitin. Bandgap optimization of perovskite semiconductors for photovoltaic applications, Chemistry A European Journal., 24, 2305-2316, 2018.
- [60] O. Erken, M. Gunes, D. Ozaslan, C. Gumus. Effect of the deposition time on optical and electrical properties of semiconductor ZnS thin films prepared by chemical bath deposition, Indian Journal of Pure & Applied Physics., 55, 471-477, 2017.
- [61] O. Oluwatoyin. Preparation and Characterization of ZnS Thin Films Grown by Spin Coating Technique, Tanzania Journal of Science, 46, 534-547, 2020.
- [62] I. Ezenwa, N. Okereke. Effects of Ligand on the Absorbance and Transmittance of Chemical Bath Deposited Zinc Sulphide Thin Film, Advances in Applied Science Research, 3 (2012) 2821-2825.
- [63] D. Hile, H. Swart, S. Motloung, E. Motaung. Effect of hydrazine hydrate as complexing agent in the synthesis of zinc selenide thin

- films by chemical bath deposition, *Thin Solid Films*, 2020; <https://doi.org/10.1016/j.tsf.2019.137707>.
- [64] H. Fekadu, B. Dejene. Chemosynthesis of nanostructures lead sulphide thin films from triethylamin (Et_3N) complexing agent, *Inorganic Chemistry Communications*, 2020; <https://doi.org/10.1016/j.inoche.2019.107583>.
- [65] G. Yadu, K. Deshmukh. Study of Ho doped (Cd-Ag)S thin films prepared by CBD method, *Optical and Quantum Electronics*, 2021; <https://doi.org/10.1007/s11082-021-02828-9>.
- [66] M. Kazi, B. Asfia, P. Sultana. Chemical bath deposition of aluminum doped zinc sulfide thin films using non-toxic complexing agent: Effect of aluminum doping on optical and electrical properties, *AIP Advances*, 2020; <https://doi.org/10.1063/5.0011191>.
- [67] U. Chalapathi, S. Park, W. Choi. Chemically grown highly crystalline PbS thin films with ethylenediamine tetraacetic acid complexing agent, *Materials Science in Semiconductor Processing*, 2021; <https://doi.org/10.1016/j.mssp.2021.106022>.
- [68] R. Gaitan, A. Gonzalez, J. Garcia. Cubic tin sulfide thin films by a Sn-NTA system based chemical bath process, *Materials Letters*, 2021; <https://doi.org/10.1016/j.matlet.2020.129222>.
- [69] S. Sengupta, M. Pateria. Structural and optical properties of Pr doped CuInS_2 thin films synthesized by chemical bath deposition, *IOP Conference Series: Materials Science and Engineering*, 2021; <https://doi.org/10.1088/1757-899X/1120/1/012013>.
- [70] K. Demir. The investigation of the corrosion behavior of CZTS thin films prepared via electrodeposition, *Materials Science in Semiconductor Processing*, 2021; <https://doi.org/10.1016/j.mssp.2020.105553>.
- [71] B. Yesica, A. Luis. Chemically deposited PbS thin films by reaction media with glycine for use in photovoltaics, *Materials Science in Semiconductor Processing*, 2021; <https://doi.org/10.1016/j.mssp.2020.105405>.
- [72] Y. Hadeethi, M. Mkawi, A. Omar, E. Bekyarova. Solvothermal synthesis of kesterite $\text{Cu}_2\text{ZnSnS}_4$ nanocrystals: Influence of glycine complexing agent concentration on properties, *Ceramics International*, 2021; <https://doi.org/10.1016/j.ceramint.2020.12.287>.
- [73] P. Offor, S. Ude, F. Otung, G. Whyte, A. Bashir. Effect of concentration of trisodium citrate complexing agent on spray-synthesized ZnS thin films, *Materials Today*, **36**, 133-140, 2021.