

2022

TRICHODERMA SPP. IN CULTURAL HERITAGE MURAL PAINTINGS OF ANCIENT EGYPTIAN TOMB, THEIR ANTIFUNGAL AND BIOACTIVITY

Abeer ElHagrassy

Associate professor at Faculty of Archaeology, Fayoum University, Egypt, afa01@fayoum.edu.eg

Follow this and additional works at: <https://digitalcommons.aaru.edu.jo/jguua>



Part of the [History Commons](#), and the [History of Art, Architecture, and Archaeology Commons](#)

Recommended Citation

ElHagrassy, Abeer (2022) "TRICHODERMA SPP. IN CULTURAL HERITAGE MURAL PAINTINGS OF ANCIENT EGYPTIAN TOMB, THEIR ANTIFUNGAL AND BIOACTIVITY," *Journal of the General Union of Arab Archaeologists*: Vol. 7: Iss. 2, Article 10.

Available at: <https://digitalcommons.aaru.edu.jo/jguua/vol7/iss2/10>

This Article is brought to you for free and open access by Arab Journals Platform. It has been accepted for inclusion in Journal of the General Union of Arab Archaeologists by an authorized editor. The journal is hosted on [Digital Commons](#), an Elsevier platform. For more information, please contact rakan@aarj.edu.jo, marah@aarj.edu.jo, u.murad@aarj.edu.jo. Published by Arab Journals Platform, 2021.

TRICHODERMA spp. IN CULTURAL HERITAGE MURAL PAINTINGS OF ANCIENT EGYPTIAN TOMB, THEIR ANTIFUNGAL AND BIOACTIVITY

BY

Abeer El Hagrassy

Associate Professor at Faculty of Archaeology, Fayoum University, Egypt

ABSTRACT

[AR] النشاط الحيوى وضد الفطرى للتريكوديرما فى التراث الثقافى للصور الجدارية فى مقبرة مصرية قديمة
لقد تم عزل أجناس فطر التريكوديرما *Trichoderma spp* من أسطح الصور الجدارية بمقبرة «نفر-باو-بتاح». لقد تعرضت هذه المقبرة سابقاً فيعام 2007 لهجوم ميكروبي مُمثل فى *A. niger* و *A. flavus* و *Alternaria alternata* فى عام 2019 تم عزل فطر الاسبرجلس نيجر فقط، بالإضافة إلى عزل أنواع من فطر التريكوديرما والى لم يتم عزلها من قبل خلال عام 2007. لقد تم تحديد ثلاثة أجناس من فطر التريكوديرما وفقاً لتأثيرها الحيوى على *A. niger* و *A. flavus* و *A. alternata* ومن خلال تسلسلها فى GenBank إلى *Trichoderma harzianum* و *T. aureoviride* و *hamatum*. ولقد تم تحليل اللوحات الجدارية فى حجرة الدفن بتقنية تحليل EDX الذى أظهر أن الطبقة الأرضية تتكون من الكوارتز والكالسيت والجبس، بينما أظهر تحليل المواد الملونة استخدام الألوان المتمثلة فى الأخضر المصرى والأزرق المصرى والهيمايتيت. ولقد أثبت تحليل الرامان أن الوسيط اللوني المُستخدم كان بمثابة وسيط صفار البيض. لقد تم قياس المواد الملونة باستخدام جهاز السبيكتروفوتوميتر مرتين: الأولى خلال عام 2007 والثانية بعد نمو *Trichoderma* خلال عام 2019. ولقد أظهرت النتائج أن عملية التمثيل الغذائى خارج الخلية لفطر التريكوديرما اثر على اللون الأزرق المصرى والأخضر المصرى وتجدر الإشارة إلى أن نتائج التحليل قد أظهرت قدرة فطر التريكوديرما على تثبيط نمو *A. niger* و *A. flavus* و *Alternaria alternata*، والى تم العثور عليها سابقاً خلال عام 2007م. ولقد تم تحديد العوامل القياسية لتعزيز نمو فطر التريكوديرما، حيث أظهرت النتائج أن 5٪ من (1: 1) $\text{NaCl} : \text{NaNO}_3$ كان بمثابة أفضل تركيز للنشاط المضاد للفطريات لجميع أنواع *Trichoderma* عند درجة الحرارة الواقعة بين 30 و 35 درجة مئوية فى وسط حمضى. تجدر الإشارة إلى أن عملية الحفظ الحيوى للتراث الثقافى مازالت قليلة الاستخدام فى نطاق الشرق الأوسط، وهى تعتبر منهجية علمية وتقنية علاج صديقة للبيئة، وذلك مع الأخذ فى الاعتبار للمخاطر التى تُسبب التغير اللوني، بالإضافة إلى كونها تقنية سهلة التطبيق، حيث يُمكن تطبيقها فى نطاق الحيز المكاني والبيئات المفتوحة أو فى نطاق المتاحف.

[EN] *Trichoderma spp.* was isolated from the mural paintings' surfaces of the tomb of Nefer-Bau-Betah. This tomb was previously deteriorated in 2007 by *Aspergillus niger*, *A. flavus*, and *Alternaria alternata* but in 2019, the tomb was deteriorated by only *A. niger*, and *Trichoderma* species that had not been isolated before in 2007. Three species of *Trichoderma* were identified according to their bioactivity effect on these microorganisms and by their sequences in the GenBank to *Trichoderma harzianum*, *T. hamatum*, and *T. aureoviride*. Furthermore, mural paintings in the burial chamber were characterized by EDX analysis which indicated that the ground layer consisted of Quartz, Calcite and Gypsum, while the pigments were characterized as Egyptian green, Egyptian blue, and hematite (Fe_2O_3). The binding media was egg yolk according to the spectrum of Raman spectroscopy. The pigments were assayed by the spectrophotometer but it caused a little effect in the color change of the pigment inside the tomb especially the blue and green Egyptian pigments, while it caused less effect in the color change of red hematite pigment. The optimization factors for increasing the bioactivity of the *Trichoderma spp.* were 5% of sodium nitrate and sodium chlorine that crystallize in the tomb, where the average temperature is between 30:35°C in acidic pH (pH=5.5). These conditions helped *Trichoderma* species to grow and work as antifungal factors in the tomb *A. niger*, *A. flavus*, and *Alternaria alternata*. *Trichoderma spp.* can be used as a new methodology for controlling the deterioration of cultural heritage. It is an eco-friendly methodology, risk-free when controlling the color change, and easy to apply anywhere in *vivo* or *vitro* in cultural heritage found in open air or in the museums.

KEYWORDS: Applied microbiology, *Aspergillus*, Bioactivity, Biotreatments, biodeterioration, color changes, mural paintings, pharaonic tomb, *Trichoderma*.

I. INTRODUCTION

Biodeterioration of cultural heritage is considered as one of the most critical factors that may destroy the mural paintings, while other environmental factors like relative humidity, salts, organic matter, and high temperatures help in increasing the deterioration effect of the microorganisms¹.

Microorganisms in cultural heritage may cause biomechanical deterioration due to the growth or penetration of them or their parts such as hyphae, mycelium, fruiting bodies, and extensive root systems inside the pores of the stone and mural paintings which leads to cause cracks or micro-cracks². Otherwise, it causes biochemical deterioration resulting from metabolic processes. Microorganisms can react with the mural painting minerals by their acids and enzymes or even toxic products. These acids decompose the minerals of pigments and shed layers by producing salt and chalets. When the soluble salts or chalets crystalize, they cause stresses in the mural paintings' pores resulting in cracks³. In addition to the aesthetic biodeterioration, the growth of microbes on the mural paintings' surfaces cover the pigments and destroy historical evidence⁴.

Conservators around the world applied numerous methodologies to prevent the cultural heritage from biodeterioration, including physical treatments of radiation⁵, fumigation⁶, low-temperature helium⁷, essential oils⁸, chemical treatments by biocides⁹, applied nanoparticles¹⁰ and bio-control by valuable microbes cells¹¹.

Trichoderma strains were well known for their anti-microbial ability towards fungi by their bio-control agents. The production of secondary metabolites by *Trichoderma* strains showed high application potential in the cultural heritage field¹². Although, *Trichoderma* species were well-known producers of enzymes essentially cellulases, Tanshinone IIA, Tanshinone I, and chitinases¹³. These enzymes could control the growth and activity of fungi¹⁴.

Bio-cleaning treatment methodology is not widespread in Egyptian tombs and the cultural heritage field, it is still a new field in Egypt. In 2007, numerous fungi were isolated from the tomb Nefer Bou Betah, like *Aspergillus niger*, *Aspergillus flavus*,

¹ CRISPIM & GAYLARDE 2005: 1-9; FAVERO -LONGO & VILES 2020: 100.

² STERFINGER 2010: 47-55; BJELLAND & ET AL. 2011: 434-442; BARTOLI & ET AL. 2014: 157-165.

³ ADAMIAK & ET AL. 2017: 2448; DYDA & ET AL. 2019: 416.

⁴ EL HAGRASSY 2018: 43 – 50.

⁵ DRÁBKOVÁ & ET AL. 2018: 75-80.

⁶ KHAIRY & ET AL. 2019: 289-300.

⁷ TURNAU & ET AL. 2020: 126485

⁸ PALLA & ET AL. 2020: 730.

⁹ FIDANZA & CANEVA 2019: 271-286; KAKAKHEL & ET AL. 2019: 104721.

¹⁰ GALDIERO & ET AL. 2011: 8894-8918; REYES-ESTEBANEZ & ET AL. 2018:1-11.

¹¹ EL HAGRASSY & HAKEEM 2018: 43-50; TURNAU & ET AL. 2020: 126485

¹² KESZLER & ET AL. 2000: 421-424; HOELL & ET AL. 2005: 180-186.

¹³ STERNBERG & DOVAL 1980: 181-192; DI PIETRO & ET AL. 1993: 308-313; MING & ET AL. 2012:330-333.

¹⁴ LOEPPKY & ET AL. 1983: 798-799; SEGUIN & ET AL. 1995: 445-448; KLEIN & EVELEIGH 1998: 57-69; HARMAN & ET AL. 2004: 43-56.

Penicillium, *Alternaria*, *Rhizopus*¹⁵. The black fungi as *Aspergillus niger*, *Alternaria*, and *Rhizopus* were a problem and caused a color change in the tomb pigments. In 2020, species of *Trichoderma* were isolated from the same mural paintings in Nefer- Bau- Betah tomb, and a crystalline salt has deteriorated the mural paintings.

II. MATERIAL AND METHODS

1. Scanning Electron Microscope {SEM}

The scanning electron microscope was used for characterizing the Mural painting's structure. The model of the SEM was Philips XL 30, Jeol JSM (5600 LV) used for micrographs. The SEM microscope was associated with the EDX Unit, «30 KV. The image magnification started from (10x to 400.000x), with the resolution for W. about (3.5nm) ». The samples were examined without coating by gold, and the conductive layer had not been sputtered. The examination was applied on the whole sample as a map not as points.

2. Raman Spectroscopy

The spectroscopy was applied via a laser beam with an average wavelength of 785nm, the power was 25 MW while the aperture setting was 50*1000 µm. The cross-sections were scanned twice, and the spectrometer calibration was obtained from a silicon crystal in which the «Raman signal was at 520.5cm⁻¹».

3. Spectrophotometer

Color –E Y E- 3100- Spectrophotometer – operation manual, S D L Company. To essay the color change of the mineral pigments, primary points were selected. These points were measured both in 2007 and 2019 to indicate the ΔE according to this equation:

$$\Delta E_{ab}^* = \sqrt{(L_2^* - L_1^*)^2 + (a_2^* - a_1^*)^2 + (b_2^* - b_1^*)^2}$$

, (L) indicates lightness, (a) is (green/ red) coordinate, and (b) is blue / yellow coordinate.

4. Fungal Strains

Fungi used in this study were obtained as follows:

- A. *Aspergillus niger*, *Aspergillus flavus*, *A. alternate* that were previously isolated in summer 2007 and identified by (El Hagrassy; 2010). The identification of fungi genus was carried out according to their morphology and spore structures. (Richardson and Watling, 1997). Each single fungi was inoculated in 20 ml of YEA 01497, of YEM (Yeast extract media) from Sigma Aldrich and incubated for 84 h at 25°C.
- B. *Trichoderma* species were isolated from the same mural paintings in summer and winter 2019 and cultured in Petri dish containing 20ml of Czapek's Dox broth medium and incubated for 7 days at 25°C. After this step the collecting mycelium and spores inoculated (vaccination) into 50ml of PDA for another 7 days at 30°C for optimal growth.

¹⁵ EL HAGRASSY 2010: 163

5. Bioactivity Media

(PDA) Potato dextrose agar powder was used to determine the bioactivity of *Trichoderma* sp. against *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata*. The commercial PDA NutriSelect® Plus consist of 20g of Dextrose, 15 g Agar, 4g Potato extract in addition to Chloramphenicol, VETRANAL® about 25mg/L with a final pH of 5.6 +/- 0.2 at 25°C.

6. Antifungal Activity

The biculture test method was prepared according to (Soytong and Quimio; 1989). A growing mycelium plugs disc (0.5 cm-diameter) was taken from the edge of PDA plate for each *Trichoderma* spp. and transferred to one side of a PDA plate about 2.0 cm from the center of the 9 mm Petri dishes). An agar disc of *Aspergillus niger*, *Aspergillus flavus*, and *A. alternata* was placed on the other side of the plate.

For positive control treatment, an agar disc of *Aspergillus niger*, *Aspergillus flavus*, and *A. alternata* were placed in the center of the Petri dish (9mm diameter). All plates were incubated at 28±2°C until the colony of control grew to a full plate.

Colony diameter was measured using a measuring ruler. The percentage of the growth inhibition was calculated using the following formula:

$$\text{inhibition} = (A-B/A) \times 100\%$$

A = colony diameter in control, B = colony diameter in biculture.

7. Identification of *Trichoderma*

For the identification of bioactive *Trichoderma* spp. the mycelium plugs of *Trichoderma* growing on PDA were taken using a (0.5-cm-diameter) cork borer and transferred to Czapek's Dox broth according to (Allen, 1950) in 500 ml flask. All flasks were incubated in a shaken incubator at 25°C for 7-10 days, then the DNA was extracted and purified by the DNA PowerPlant® Pro Kit (Qiagen, Milan, Italy).

The identification was carried out by amplification and analysis of the regions of the (ITS) region of ribosomal DNA (RDNA) *Internal Transcribed Spacer*. The amplification was made by *Taq* DNA polymerase, recombinant (Invitrogen, Milan, Italy) with the universal primer pair ITS 5 and 4 regions of the ribosomal RNA gene cluster sequences according to the method described¹⁶ as ITS 5 «(50-GGAAGTAAAAGTCGTAACAAGG-30)» and ITS-4 «(50-TCCTCCGCTTATTGATATGC-30)».

PCR amplification mixture reaction carried out using PCR buffer «(1X), dNTP mixture (0.2 mm), MgCl₂ (1.5 mm) », forward and reverse primers (0.5 mm), *Taq* DNA Polymerase (1 U), and 100 ng of DNA.

Thermo-cycler conditions were: 94° C for 3 min in a «C1000 Touch™ Thermal Cycler (Bio-Rad, Munich, Germany)» followed by 35 cycles of 0.5 min at 94°C, 0.5 min at 55°C, 0.5 min at 72°C, and ending with 10 min at 72°C. Amplified DNA products were analyzed using electrophoresis in 1% agarose gels run in Tris/borate/EDTA buffer and sequenced in the Scientific Research Center of the Biotechnology, Lebanon. Obtained sequences were analyzed using FinchTV¹⁷ v.1.4.0¹⁸. The sequencing data were compared with the GenBank database¹⁹.

¹⁶ THE METHOD DESCRIBED BY WHITE & ET AL. 1990.

¹⁷ FINCH: «FINCHTV 1.4», <https://finchtv.software.informer.com/1.4/>

Accessed on 13 /08 2020.


III. RESULTS

1. Structure of Nefer Bau Betah Mural Painting

Fragments were taken from ground layer and pigments of the mural painting.

A. Ground Layer


The SEM- EDX analysis showed that the ground layer consisted of Calcite " CaCO_3 " therefore the presence of (Ca, O & C). In addition to the Quartz " SiO_2 " due to the existence of (Si, O) element, as well Gypsum " CaSO_4 " considering the presence of (Ca, S, O) elements [FIGURE 1].

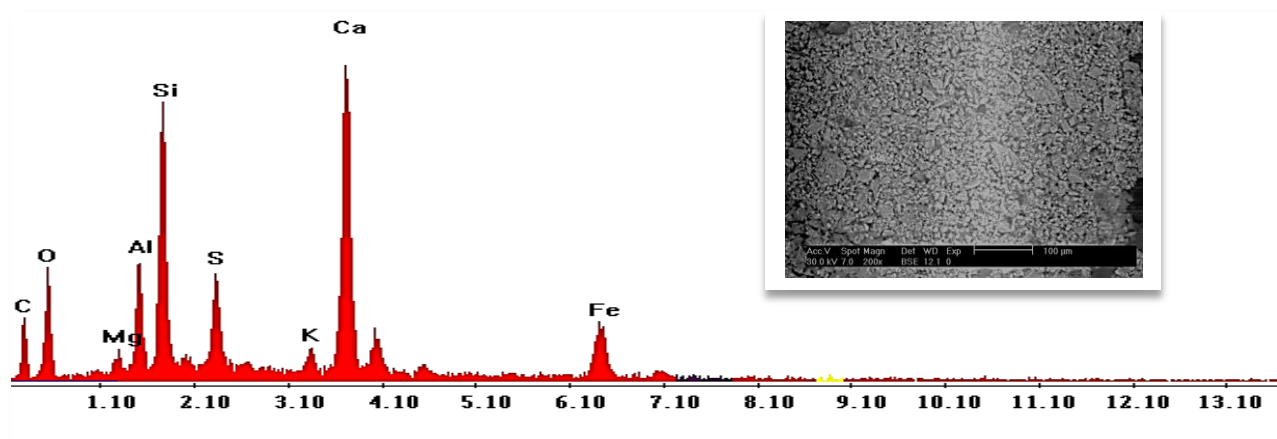

[FIGURE 1]: EDX *spectrum* the component elements consisted the ground layer of the mural paintings 500x, Acc V =30KV, spot 7, Det: BSE, WD: 12.1, scale: 100 μm

B. Pigments

Small fragments of the pigments were investigated and analyzed by SEM-EDX. The analysis showed that, the green pigment was Egyptian green (CaSiO_3), [FIGURE2], the blue pigment was Egyptian blue ($\text{CaCuSi}_4\text{O}_{10}$) as shown in [FIGURE 3], and the red pigment is hematite (Fe_2O_3), [FIGURE 4].

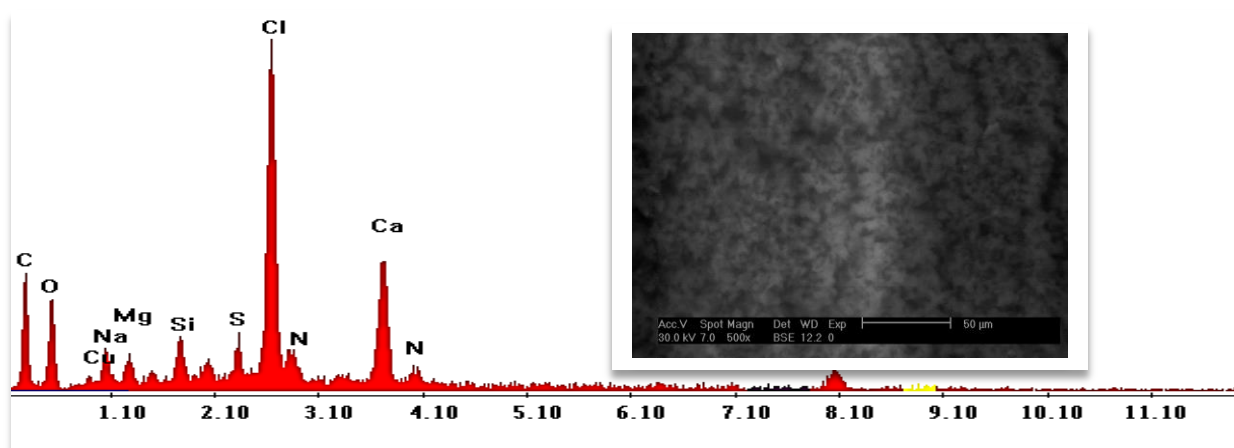


[FIGURE 2]: EDX *spectrum* the component elements consisted the Green pigment of the mural paintings 500x, Acc V =30KV, spot 7, Det: BSE, WD: 12.2, scale: 100 μm .


¹⁸ FINCH: «FINCHTV 1.4», (<https://finchtv.software.informer.com/1.4>)

Accessed on 13 /08 2020.

¹⁹ GENE BANK: «Basic Local Alignment Search Tool», <https://blast.ncbi.nlm.nih.gov/Blast.cgi> Accessed on 13/08 2020.

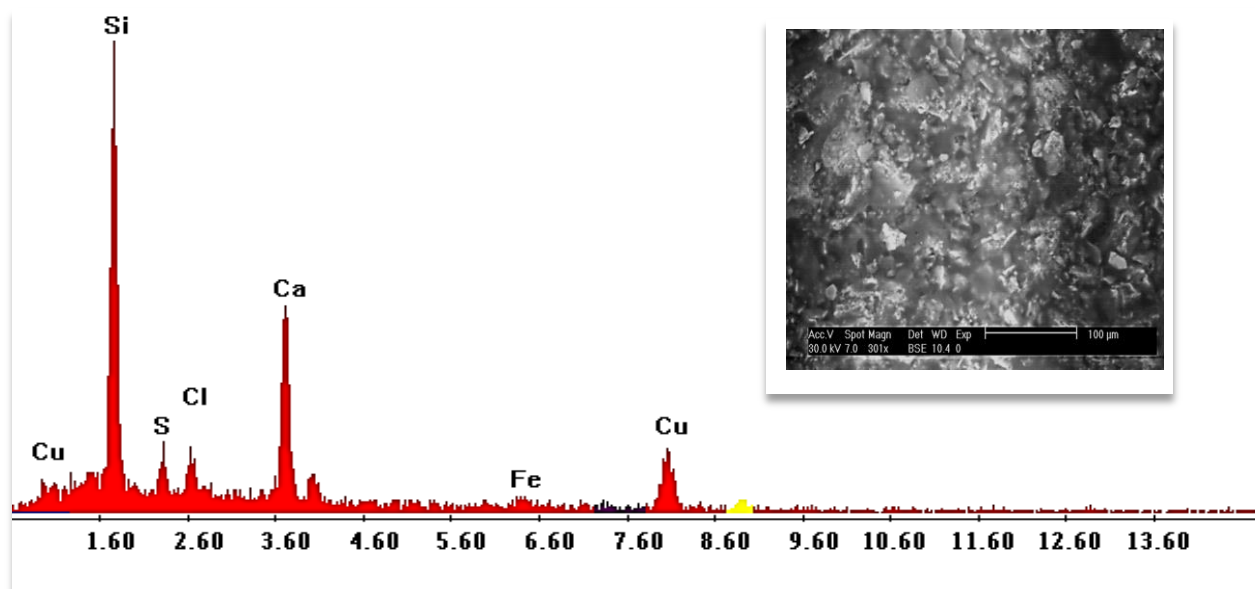


[FIGURE 3]: EDX *spectrum* the component elements consisted the Blue pigment of the mural paintings 500x. Acc V =30KV, spot 7, Det: BSE, WD: 10.4, scale: 100μm.

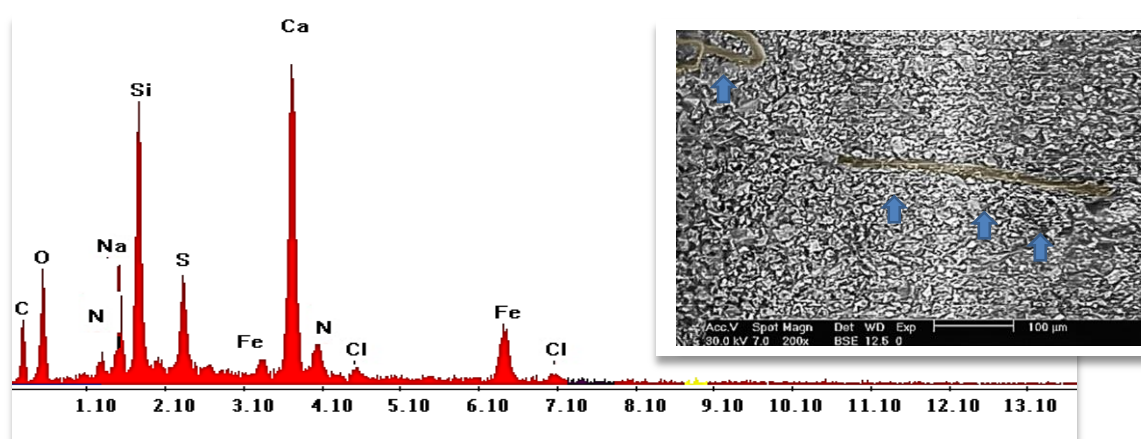

[FIGURE 4]: EDX *spectrum* the component elements consisted the red pigment of the mural paintings with the presence of mycelium 200x, Acc V =30KV, spot 7, Det: BSE, WD: 12.5, scale: 100μm.

C. Binding Medium

Raman spectra showed a slight degree of egg yolk that was used as a binding media. The sample was characterized due to the presence of the functional groups as follows: (n=CH) in 3007, (n=CH) in 2927, (C=C) in 1667, (d- CH) in 1442, (C≡H) in 1265 and (C-O) in 1156 as presented in [FIGURE 5].

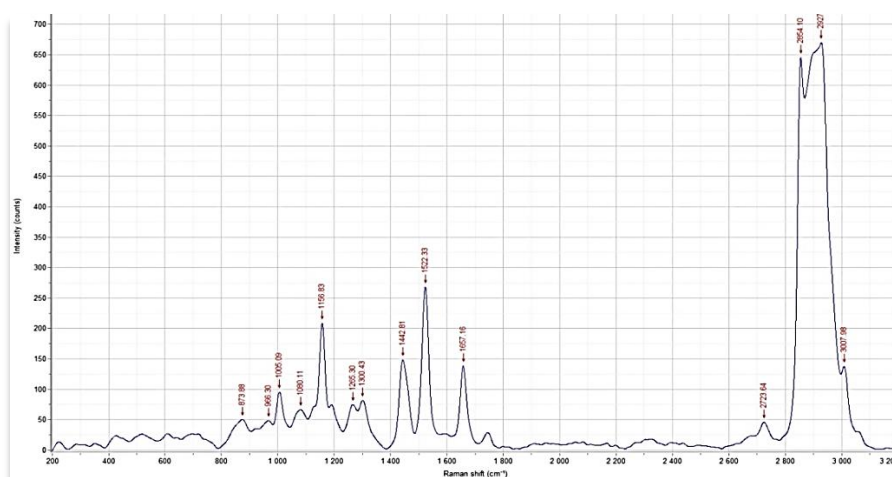

[FIGURE5]: The spectra presented the use of egg yolk as a binding media of the pigment.


D.Deterioration Phenomena

Three main factors should be studied to understand the deterioration factor; first; the environmental conditions inside the tomb, especially after it was closed for five years, second; the crystallization of salts inside the tomb [FIGURE 6], and third; the different species of microorganism affecting the mural painting's structure that changes with time [FIGURE 7].



[FIGURE 6]: A: the crystallization of salts over the pigments, B: The SEM of the salts (200X).


© Photo taken by the researcher

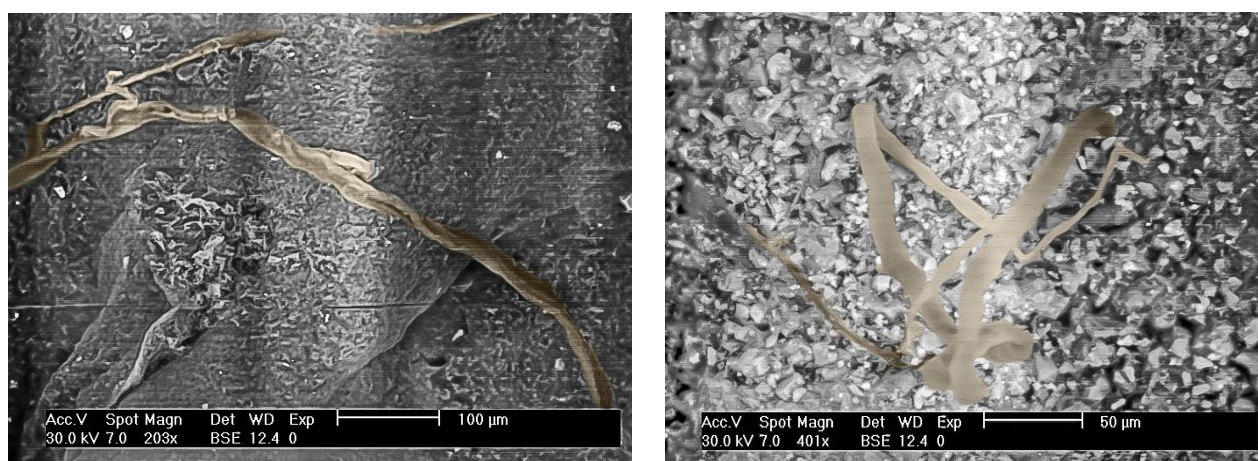

[FIGURE 7]: The mycelium penetrate the mural paintings layer. (200x, 400x)

E. Identification of Microorganisms

During the four seasons in 2019 swabs analysis were taken to culture the microorganisms and compared with the microorganisms that had previously deteriorated the tomb in 2007 and in 2019 [FIGURE 8].

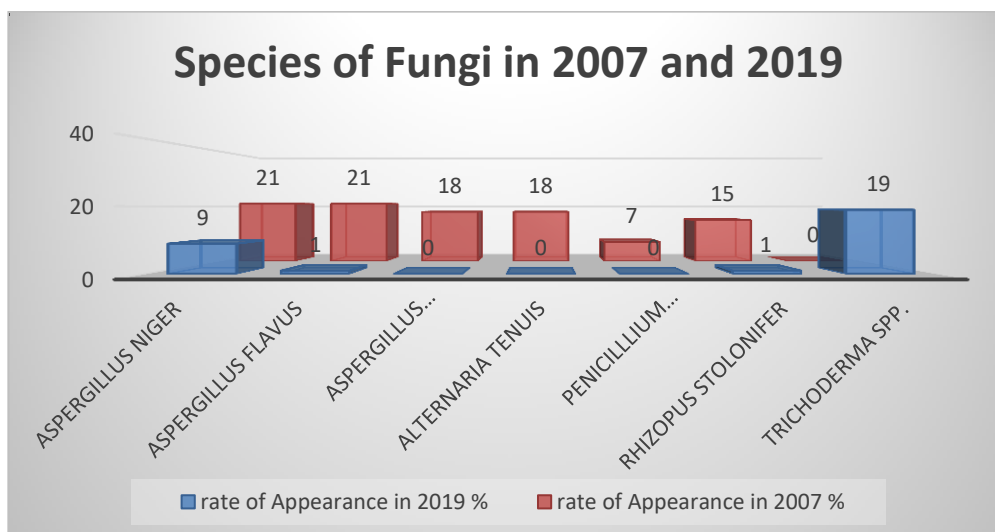

[FIGURE 8]: The species of fungi founded in 2007 and on 2019.
© Designed by the researcher


The tomb was closed particularly from 2011 to 2017, then re-opened for conservation in 2018 after crystallization of salts over the wall paintings. The swabs in 2019, showed that the tomb deteriorated with *Aspergillus niger* and species of *Trichoderma* [FIGURE 9].



[FIGURE 9]: The deterioration of the tomb by salts and Biodeterioration effects.
© Photo taken by the researcher

F. Environmental Condition

The environmental conditions inside the tomb in both 2007 and 2019 were with average high temperature from 18 to 35°C, and the average low temperature 8 to 11°C in 2007 and from 9 to 10 °C in 2019, while the average relative humidity from 45 to 59% in 2007 and from 46 to 61% in 2019 [FIGURE 10].

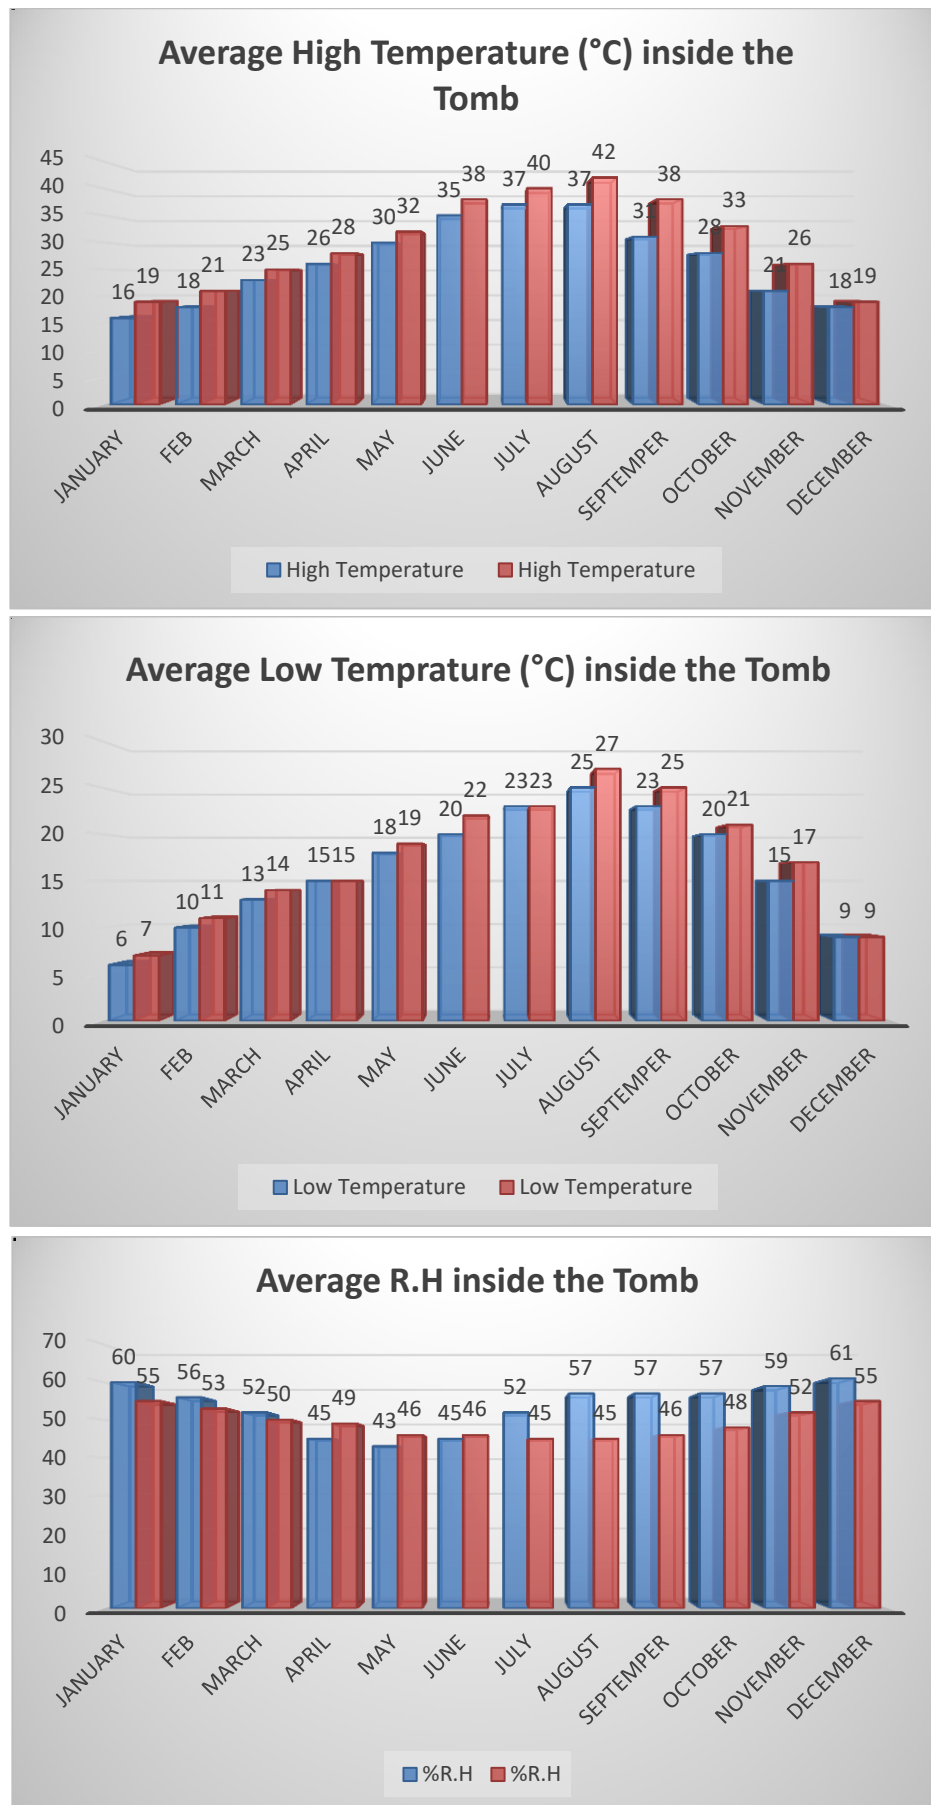

[FIGURE 10]: The environmental condition inside the tomb in 2007 and 2019.

© Designed by the researcher

G. Color Change by Colorimeter

The data showed that the color change (ΔE) for the pigments in the tomb were less than 5 which is in the safe range as presented in [TABLE 1].

Pigments	2007			2019			ΔE
	ΔL	Δa	Δb	ΔL	Δa	Δb	
Red	53.53	-1.98	13.47	52.98	-3.29	13.11	1.51
Blue	-54.53	-1.77	36.26	-53.51	-3.34	35.15	2.66
Green	-59.45	-45.98	55.03	-57.90	-43.59	54.79	2.86

[TABLE 1]: The color change for the main pigments inside the tomb in 2007 and 2019.

© Designed by the researcher

H. Antifungal Activity and the Identification of Active *Trichoderma* spp

The positive control of *Aspergillus niger*, *Aspergillus flavus*, and *A. alternata* grew faster and significantly formed a large colony in the control plate; the growth diameter was about 8.89; 8.81; 8.71, respectively. According to the biculture plate, only three species of *Trichoderma* affected the growth rate of the three fungi *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata*. The effective *Trichoderma* species were identified according to the GenBank as «*Trichoderma harzianum*, *T. hamatum*, and *T. aureoviride*».

The antifungal activity of the three *Trichoderma* species were assayed as illustrated in [TABLE 2].

Fungi	<i>A. niger</i>		<i>A. flavus</i>		<i>Alternaria alternata</i>	
	Colony diameter (mm)	Inhibition %	Colony diameter (mm)	Inhibition %	Colony diameter (mm)	Inhibition %
Control	8.89	0	8.81	0	8.71	0
<i>Trichoderma harzianum</i>	4.52	65.12	3.23	63.33	2.11	75.77
<i>T. aureoviride</i>	4.16	48.14	3.35	61.97	2.24	74.28
<i>T. hamatum</i>	4.66	4.58	3.09	64.92	2.36	72.90

[TABLE 2]: Antifungal effects of *Trichoderma* spp. on *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata*. © Designed by the researcher

1. Optimisation of Antifungal Activity

The tomb was deteriorated by three main factors. First, salt crystallization. Second, the temperature inside the tomb. Third, poor ventilation which increases humidity, especially inside the burial chamber.

A. Salt Concentration

According to the EDX analysis, the tomb was deteriorated by two types of salts, sodium nitrate, and sodium chloride. To detect the effect of salt on growth and antifungal

activity, after incubation for 14 days in a shaker, different concentrations of NaCl: NaNO₃ (1: 1) from 0 to 5% were carried out. In the end, the biomass accumulations for each concentration were dried and weighed, the percentage of inhibition was calculated according to t Topps and Wain equation methodology²⁰, as represented in the [TABLE 3]

NaCl:NaNO ₃ (1: 1) Salt concentration	<i>Trichoderma</i> spp. Dry weight		Growth Reduction (%)		
			<i>A. niger</i>	<i>A. flavus</i>	<i>Alternaria alternata</i>
0	<i>T. harzianum</i>	0.36± 0.01	23.1±0.4	31.6±0.26	36±0.3
	<i>T. hamatum</i>	0.37±0.1	18.6±0.2	20.12±0.1	18.5±0.36
	<i>T. aureoviride</i>	0.39±0.1	19.6±0.1	19.1±0.37	20.1±0.01
1	<i>T. harzianum</i>	0.38±0.02	30.4±0.1	32.2±0.26	36.9±0.006
	<i>T. hamatum</i>	0.40±0.001	19.2±0.34	22±0.001	19.14±0.01
	<i>T. aureoviride</i>	0.39±0.001	20.3±12	22.3±0.01	21.8±0.42
2	<i>T. harzianum</i>	0.38±0.02	32±0.42	33±0.01	41.3±0.24
	<i>T. hamatum</i>	0.41±0.1	23.53±0.23	24.2±0.04	23.75±0.3
	<i>T. aureoviride</i>	0.40±0.001	23.4±0.02	24.98±0.25	25.3±0.1
3	<i>T. harzianum</i>	0.39±0.002	45.8±0.54	49.2±0.002	48.9±0.36
	<i>T. hamatum</i>	0.43±0.2	31.82±0.65	29.86±0.14	31.56±0.001
	<i>T. aureoviride</i>	0.44±0.1	27.12±0.7	28.6±0.01	30.12±0.02
4	<i>T. harzianum</i>	0.44±0.001	51.3±0.2	53.21±0.1	53.28±0.003
	<i>T. hamatum</i>	0.43±0.02	33.1±2.3	33.6±14	33.9±0.1
	<i>T. aureoviride</i>	0.41±0.002	31.98±0.2	31.9±0.7	35.13±0.01
5	<i>T. harzianum</i>	0.46±0.002	52.12±0.5	52.4±0.32	53.6±0.12
	<i>T. hamatum</i>	0.45±0.001	33.69±0.1	36.12±45	35.9±21
	<i>T. aureoviride</i>	0.40±0.001	33.15±0.4	33.7±0.25	35.64±0.23

[TABLE 3]: Dry weights of *Trichoderma harzianum*, *T. hamatum*, and *T. aureoviride*. and its Antifungal activity expressed as % of the growth reduction of the *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata* at different salt concentration. © Designed by the researcher

B: Temperature

To assay, the effect of temperature, different degrees from 20°C to 50°C were applied and essayed its effect on the growth and antifungal activity after incubation for 14 days in a shaker. The biomass accumulations were dried and weighed, as represented in the [TABLE 4].

²⁰ TOPPS & WAIN 1957: 506-511.

Temperature (°C)	Trichoderma spp. Dry weight		Growth Reduction (%)		
			<i>A. niger</i>	<i>A. flavus</i>	<i>Alternaria alternata</i>
20	<i>T. harzianum</i>	0.21±0.1	24.16±0.3	20.13±0.65	18.21±0.64
	<i>T. hamatum</i>	0.23±0.001	29.32±0.001	28.11±0.01	25.12±0.06
	<i>T. aureoviride</i>	0.25±0.1	31.22±0.11	34.24±0.25	37.23±0.007
25	<i>T. harzianum</i>	0.24±0.002	45.23±0.14	43.32±0.1	39.32±0.6
	<i>T. hamatum</i>	0.26±0.01	48.32±0.35	48.2±0.004	47.32±0.1
	<i>T. aureoviride</i>	0.25±0.06	45.21±0.17	46.98±0.3	47.98±0.1
30	<i>T. harzianum</i>	0.48±0.002	56.3±0.4	55.21±0.01	58.6±0.21
	<i>T. hamatum</i>	0.39±0.3	51.36±0.1	64.93±0.87	50.36±0.41
	<i>T. aureoviride</i>	0.40±0.6	48.37±0.1	50.33±0.12	52.69±0.005
35	<i>T. harzianum</i>	0.41±0.25	54.31±0.02	52.4±0.21	55.24±0.2
	<i>T. hamatum</i>	0.43±0.06	54.1±0.2	67.12±0.3	49.65±0.001
	<i>T. aureoviride</i>	0.45±0.004	50.71±0.8	52.3±0.04	55.36±0.01
40	<i>T. harzianum</i>	0.46±0.6	40.32±0.1	45.21±0.25	50.21±0.03
	<i>T. hamatum</i>	0.37±0.1	38.21±0.04	39.54±0.36	36.51±0.01
	<i>T. aureoviride</i>	0.40±0.7	36.65±0.1	39.74±0.42	37.62±0.69
45	<i>T. harzianum</i>	0.41±0.001	35.21±0.74	33.96±0.1	31.6±0.2
	<i>T. hamatum</i>	0.31±0.8	31.23±0.2	32.6±0.81	31.12±0.5
	<i>T. aureoviride</i>	0.35±0.01	30.6±12	31.21±0.4	30.61±0.03
50	<i>T. harzianum</i>	0.30±0.01	28.12±0.3	24.31±0.65	20.17±0.64
	<i>T. hamatum</i>	0.29±0.3	29.32±0.001	28.11±0.01	25.12±0.06
	<i>T. aureoviride</i>	0.29±0.01	25.21±0.18	24.54±0.32	20.69±0.23

[TABLE 4]: Dry weights of *Trichoderma harzianum*, *T. hamatum*, and *T. aureoviride*." and its Antifungal activity expressed as % of the growth reduction of the *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata* at different temperature. © Designed by the researcher

C. pH Value

The average pH from (5 to 8) was examined its effect after incubation for 14 days at 35°C by using 0.1 N HCL and 0.1 N NaOH. The biomass accumulations were dried and weighed, as represented in the [TABLE 5].

pH Value	<i>Trichoderma</i> spp. Dry weight		Growth Reduction (%)		
			<i>A. niger</i>	<i>A. flavus</i>	<i>Alternaria alternata</i>
5	<i>T. harzianum</i>	0.47±0.024	46.23±0.07	50.1±0.06	51.62±0.06
	<i>T. hamatum</i>	0.44±0.001	45.91±0.01	42.31±0.07	50.41±0.02
	<i>T. aureoviride</i>	0.40±0.32	41.23±0.06	51.01±0.001	51.36±0.9
5.5	<i>T. harzianum</i>	0.49±0.063	58.98±0.12	60.23±0.2	67.32±0.12
	<i>T. hamatum</i>	0.46±0.004	56.14±0.65	57.36±0.001	60.32±0.01
	<i>T. aureoviride</i>	0.44±0.17	52.13±0.1	53.62±0.22	57.32±0.23
6	<i>T. harzianum</i>	0.33±0.52	0.13±0.007	0.55±0.01	0.38±0.21
	<i>T. hamatum</i>	0.31±0.06	35.45±0.06	35.98±0.36	34.22±0.9
	<i>T. aureoviride</i>	0.30±0.14	36.2±0.01	38.62±0.11	40.98±0.07
6.5	<i>T. harzianum</i>	0.24±0.004	34.12±0.007	38.16±0.012	38.33±0.001
	<i>T. hamatum</i>	0.20±0.19	30.18±0.01	30.98±0.03	31.15±0.01
	<i>T. aureoviride</i>	0.19±0.001	29.26±0.07	29.88±0.045	30.19±0.07
7	<i>T. harzianum</i>	0.20±0.025	28.7±0.06	29.64±0.73	30.15±0.08
	<i>T. hamatum</i>	0.20±0.17	25.11±0.041	26.79±0.16	29.50±0.1
	<i>T. aureoviride</i>	0.19±0.1	21.33±0.4	22.14±0.01	20.36±0.41
7.5	<i>T. harzianum</i>	0.17±0.041	15.32±0.01	18.98±0.2	19.63±0.03
	<i>T. hamatum</i>	0.15±0.01	16.9±0.21	18.63±0.01	19.1±0.23
	<i>T. aureoviride</i>	0.15±0.021	14.32±0.01	14.82±0.31	14.66±0.5
8	<i>T. harzianum</i>	0.11±0.021	10.22±0.003	17.32±14	20.35±0.01
	<i>T. hamatum</i>	0.10±0.15	13.34±0.1	13.45±0.06	11.62±0.07
	<i>T. aureoviride</i>	0.08±0.021	14.23±0.21	13.98±0.01	14.25±0.03

[TABLE 5]: Dry weights of *Trichoderma harzianum*, *T. hamatum*, and *T. aureoviride*." and its antifungal activity expressed as % of the growth reduction of the *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata* at different pH value. ©Designed by the researcher

IV. DISCUSSION

According to the swabs that were previously taken from the mural paintings of the Egyptian tomb (Nefer- Bau- Betah) in 2019, species of *Trichoderma* were detected. The EDX analysis of the ground layer of the paintings consisted of calcite and gypsum which is an evidence that the tomb had been prepared by tempera technique²¹. The EDX of the pigments showed that both the blue and green pigment were ancient manufactured pigments; Egyptian blue and Egyptian green, while, the red pigment was hematite. All these pigments were mixed with a binding media. The Raman spectroscopy analysis indicated that the binding media was egg yolk. According to Lucas & Harris²², mixing the pigments with binding media was applied only when ancient Egyptians prepared tombs by tempera technique and in this case Nefer Bau Betah Tomb was decorated by the egg yolk tempera technique which is one of the most common technologies used in ancient Egypt.

The tomb of Nefer- Bau- Betah had been deteriorated in 2007 by *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata*. These three fungi were considered as the most deteriorating fungi that usually cause damage to the Egyptian mural paintings²³. Therefore, the threats posed by the biodeterioration factor have been studied in several researches in different countries²⁴. In 2019, the same tomb was badly affected by *Aspergillus niger* and species of *Trichoderma* and was deteriorated by salt crystallization.

According to the EDX analysis, two types of salts deteriorated the tomb, namely sodium chloride, and sodium nitrate. In 2007, the high temperature inside the tomb was on average from (31 to 39°C), but in 2019 the high-temperature average increased from (35 to 44°C). These temperatures were theorized as an optimized temperature for the growth of *Trichoderma*.²⁵ On the other hand, the relative humidity inside the tomb ranged from 46 to 61 %. These three main factors inside the tomb (temperature, humidity, and salt) played a main role for the growth of *Trichoderma*.

The swabs that were taken in 2019 displayed that the tomb was deteriorated by only *Aspergillus niger* and 3 species of *Trichoderma*. The growth of *Trichoderma* helped to control the growth and the bioactivity of other species that previously deteriorated the same tomb in 2007. Numerous studies have been carried out on the effect of *Trichoderma* in the inhibition of fungi.²⁶

Although *Trichoderma* saved the mural paintings from the effect of other microorganisms, it caused further effects by the color change in the natural and synthetic pigment. According to the spectrophotometer analysis, the ΔE was a little high in Egyptian blue and Egyptian green (the ΔE was about 2.5 which is easy to be noticed by the naked eye), while red hematite as a natural pigment was less deteriorated (the ΔE was

²¹NICHOLSON & SHAW 2000: 269.

²²LUCAS & HARRIS 1948: 202.

²³HELMİ & ET AL. 2009: 306.

²⁴CIFERRI 1999: 879-885; HOFFLAND & ET AL. 2004: 258-264; MILANESI & ET AL. 2006A: 168-173; MILANESI & ET AL. 2006B: 7-13; VENERANDA & ET AL. 2017: 19599-19608.

²⁵ABOU-ZEID & ET AL. 2011: 233-244; DARYAEI & ET AL. 2016A: 999-1009; DARYAEI & ET AL. 2016B: 24-30.

²⁶ZHOU & ET AL. 2017: 18-20; ZHANG & ET AL. 2018: 59-66; KHAN & ET AL. 2020: 817; ZHU & ET AL. 2020: 105161.

about 1.5 which can be neglected). This result needs special studies in the future to assay why the synthetic pigments are more sensitive than the natural pigments.

The preliminary examination for antifungal activity of all *Trichoderma* spp. showed that only three species have the ability to control the growth of "*Aspergillus niger*, *A. flavus*, *Alternaria alternata*." which were identified according to 16s DNA sequences to "*Trichoderma harzianum*, *T. hamatum*, and *T. aureoviride*." These three species of *Trichoderma* have the ability to control the growth of the other fungi.²⁷

To assess the optimum conditions three main factors were studied, first, salt crystallization inside the tomb as presented in the EDX results, where two types of salts were found: NaCl and NaNO₃, second, the temperature inside the tomb and third, pH value.

The optimum salt concentration required for the production of antifungal activity was examined with different salt concentrations (0- 5%), the sodium chloride and sodium nitrate were prepared (1:1). The data showed that 4% of NaCl: NaNO₃ (1:1) was the optimum concentration of antifungal activity²⁸ for *T. harzianum* in inhibiting the growth of *A. flavus*, while 5 % of NaCl: NaNO₃ (1:1) was the best concentration for antifungal activity of all *Trichoderma* species to control the growth rate of other fungi.²⁹

The experimental test represented that the antifungal activity of *T. harzianum* was found to be optimum at 30°C, while the 35°C was the optimum temperature for the antifungal activity for both *Trichoderma hamatum*, and *T. aureovirid*. These results corresponded with the results of Sterflinger³⁰, Hoell³¹ and Hossemi & Soltani³². The pH value was essayed to indicate the optimum value for antifungal activity of the *Trichoderma* species, the acidic 5.5 pH was the optimum value of antifungal activity of all species of *Trichoderma* and controlled the growth rate of other fungi³³.

²⁷ LORITO & ET AL. 1993: 302-307; VITERBO & ET AL. 2001:169-174; KÜÇÜK& ET AL. 2003: 247-253; SHALINI & KOTASTHANE 2007: 2272-2281; SHARMA & ET AL. 2011: 19898-19907; BAAZEEM& ET AL. 2021: 331.

²⁸ AIT-LAHSEN & ET AL. 2001: 5833–5839.

²⁹ BUGNI & IRELAND 2004: 143-163; HARMAN 2006: 190-194.

³⁰ STERFLINGER 1998: 217-281; STERFLINGER 2018: 10-12.

³¹ HOELL & ET AL. 2005: 180-186.

³² HOSSENI & SOLTANI 2014: 753–761.

³³ STEYAERT& ET AL. 2010A: 198-208; STEYAERT & ET AL. 2010B: 179-188; DARYAEI & ET AL. 2016: 999-1009.

V. CONCLUSION

In this research, two swabs were taken from the same tomb Nefer Bau Betah in 2007 and 2019. The swab analysis in 2019 showed that the microorganisms that were previously found in 2007 had disappeared and new species of *Trichoderma* were isolated. Three species of *Trichoderma* were identified according to their bioactivity effect over *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata* and by their sequences in the GenBank to «*Trichoderma harzianum*, *T. hamatum*, and *T. aureoviride*» These three *Trichoderma* species have the ability to control the growth rate of the microbes that were found in 2007. The optimization factors for increasing the bioactivity of the *Trichoderma* spp. were 5% of sodium nitrate and sodium chloride that crystallize in the tomb with an average temperature between 30:35°C in acidic pH (pH=5.5). These conditions helped *Trichoderma* species to grow and work as antifungal factors in the tomb *Aspergillus niger*, *Aspergillus flavus*, and *Alternaria alternata* but it caused a little effect in the color change of the pigment inside the tomb especially the blue and green Egyptian pigments, while it caused less effect in the color change of red hematite pigment.

Finally, the effect of the bioactivity of *Trichoderma* species on the ancient Egyptian pigments and media, and a biochemical studies for these pigments will be discussed in a future study.

BIBLIOGRAPHY

- ABOU-ZEID, N. M, ET AL: «*Trichoderma* Species in Egypt and their Biocontrol Potential against Some Plant Pathogenic Fungi», *Egyptian Journal of Biological Pest Control* 21, 2011, 233-244.
- ADAMIAK, J, ET AL.: «Untargeted Metabolomics Approach in Halophiles: Understanding the Biodeterioration Process of Building Materials», *Front. Microbiology* 8, 2017, 2448-2450.
- AIT-LAHSEN, H., ET AL: «An Antifungal exo- α -1,3-glucanase (AGN13.1) from the Biocontrol Fungus *Trichoderma harzianum*». *Applied and Environmental Microbiology* 67, 2001, 5833–5839.
- BAAZEEM, A, ET AL.: «In Vitro Antibacterial, Antifungal, Nematocidal and Growth Promoting Activities of *Trichoderma hamatum* FB10 and Its Secondary Metabolites», *Journal of Fungi* 7, 2021, 331-344.
- BARTOLI, F, ET AL.: «Biological Colonization Patterns on the Ruins of Angkor Temples (Cambodia) in the Biodeterioration vs Bioprotection Debate», *International Biodeterioration and Biodegradation* 96, 2014, 157–165.
- BJELLAND, T, ET AL: «Microbial Meta communities in the Lichen–Rock Habitat», *Environ Microbiol Rep.* 3, 2011, 434–442.
- BUGNI, T. S. & IRELAND, C. M.: «Marine-Derived Fungi: A Chemically and Biologically Diverse Group of Microorganisms», *Natural Product Report* 21, 2004, 143-163.
- CIFERRI, O.: «Microbial Degradation of Paintings», *Applied Environ. Microbiology* 65, 1999, 879-885.
- CRISPIM, C.A. & GAYLARDE, C.C.: «Cyanobacteria and Biodeterioration of Cultural Heritage: A Review», *Microbial Ecology* 49, 2005, 1-9.
- DARYAEL, A, et AL: «Effects of Temperature, Light and Incubation Period on Production, Germination and Bioactivity of *Trichoderma atroviride*», *Journal of Applied Microbiology* 120, 2016A, 999-1009.
- DARYAEL, A, ET AL: «pH and Water Activity in Culture Media Affect Biological Control Activity of *Trichoderma atroviride* Against *Rhizoctonia solani*», *Biological Control* 92, 2016B, 24–30.
- DI PIETRO, A, ET AL: «Endochitinases from *Gliocladium virens*: Isolation, Characterization and Synergistic Antifungal Activity in Combination with Gliotoxin», *Phytopathology* 83, 1993, 308–313.
- DRÁBKOVÁ, K. D., ET AL: «Influence of Gamma Radiation on Properties of Paper and Textile Fibers During Disinfection», *Radiation Physics and Chemistry* 152, 2018, 75–80.
- DYDA, M, ET AL.: «Bacterial and Fungal Diversity Inside the Medieval Building Constructed with Sandstone Plates and Lime Mortar as an Example of the Microbial Colonization of a Nutrient-Limited Extreme Environment (Wawel Royal Castle, Krakow, Poland) », *Microorganisms* 7, 2019, 416-429.
- ELHAGRASSY, A.F.: «Study for Treatments the Effect of the Microbiological Deterioration of Mural Painting Executed by Tempra Technique, Applied on Selected Models», MA Thesis of Science, Faculty of archaeology, Cairo University, 2010.
- ELHAGRASSY, A.F. & HAKEEM, A.: «Comparative Study of Biological Cleaning and Laser Techniques for Conservation of Weathered Stone in Failaka Island, Kuwait», *Scientific Culture* 4, 2018, 43-50.
- FAVERO-LONGO, S. E. & VILES, H.A.: «A Review of the Nature, Role and Control of Lithobionts on stone Cultural Heritage: Weighing-up and Managing Biodeterioration and Bioprotection», *World Journal of Microbiology and Biotechnology* 36, 2020, 100-121.
- FIDANZA, M.R. & CANEVA, G.: «Natural Biocides for the Conservation of Stone Cultural Heritage: A Review», *Journal of Cultural Heritage* 38, 2019, 271–286.

- GALDIERO, S, ET AL: «Silver Nanoparticles as Potential Antiviral Agents», *Molecules* 16, 2011, 8894-8918.
- HARMAN, G.E, ET AL: «*Trichoderma* species–Opportunistic Avirulent Plant Symbionts», *Nat Rev Microbiol* 2, 2004, 43–56
- HARMAN, G.E.: «Overview of Mechanisms and Uses of *Trichoderma* spp», *Phytopathology* 96, 2006, 190–194.
- HELMI, F.M, ET AL: «Electromagnetic Waves as a New Technique for Control *Aspergillus niger* Fungus in Ancient Egyptian Mural Paintings», 4th international Congress on Science and Technology for the Safeguard of cultural heritage in the Mediterranean Basin, Cairo, Egypt, 6-8 December 2009.
- HOELL, I.A, KLEMSDAL, S.S, ET AL: «Overexpression and Characterization of a Novel Chitinase from *Trichoderma atroviride* strain P1», *Biochim Biophys Acta* 1748, 2005, 180–186.
- HOFFLAND, E, ET AL: «The Role of Fungi in Weathering», *Front Ecol Environ* 2, 2004, 258–264.
- HSSEYNI-MOGHADDAM, M.S. & SOLTANI, J.: «Bioactivity of Endophytic *Trichoderma* Fungal Species from the Plant Family Cupressaceae», *Ann Microbiol* 64, 2014, 753–761.
- KAKAKHEL, M.A, ET AL: «Controlling Biodeterioration of Cultural Heritage Objects with Biocides: A Review», *Int. Biodeterior. Biodegrad.* 143, 2019, 104721.
- KESZLER, A, ET AL: «Separation and Identification of Volatile Components in the Fermentation Broth of *Trichoderma atroviride* by Solid phase Extraction and Gas Chromatography-Mass Spectroscopy», *Journal Chromatograph Sci.* 38, 2000, 421–424.
- KHAIRY, A., EL HAGRASSY, A. & ALI, N.: «The Effectiveness of Oxygen Absence on the Ancient Egyptian Pigments Sterilization of Ancient Painted Wooden Object Using Anoxia», *Analecta Papyrologica* 23, 2019, 289-300.
- KHAN, R.A.A, ET AL: «Bioactive Secondary Metabolites from *Trichoderma* spp. Against Phyto pathogenic Fungi», *Microorganisms* 8, 2020, 817- 832.
- KLEIN, D. & EVELEIGH, E.: *Ecology of Trichoderma*. In: Kubicek CP, Harman GE (eds) *Trichoderma and Gliocladium*, London (Taylor and Francis) 1998, 57–69.
- KÜÇÜK, Ç. & KIVANÇ, M.: «Isolation of *Trichoderma* spp. and Their Antifungal, Biochemical and Physiological Features», *Turk J Biol* 27, 2003, 247-253.
- LOEPPKY, C.B, ET AL: «*Trichoderma viride* Peritonitis», *South Med Journal* 76, 1983, 798–799.
- LORITO, M, ET AL: «Chitinolytic Enzymes Produced by *Trichoderma harzianum*; Antifungal Activity of Purified Endochitinase and Chitobiosidase», *Phytopathology* 83, 1993, 302-307.
- LUCAS, A. & HARRIS, J.R.: *Ancient Egyptian Materials and Industries*, Mineola, New York, (Dover Publication, INC.), 1948.
- MILANESIA, C.; BALDI, F.; BORIN, S.; VIGNANI, R., CIAMPOLINI, F.; FALERI, C.; CRESTI, M.: «Biodeterioration of a Fresco by Biofilm Forming Bacteria», *International Biodeterioration & Biodegradation* 57, 2006A, 168–173
- MILANESIA, C., ET AL.: «Fungal Deterioration of Medieval Wall Fresco Determined by Analyzing Small Fragments Containing Copper», *International Biodeterioration & Biodegradation* 57, 2006, 7-13.
- MING, Q., ET AL: «Tanshinone IIA and Tanshinone I Production by *Trichoderma atroviride* D16, an Endophytic Fungus in *Salvia Miltiorrhiza*», *Phytomedicine* 19, 2012, 330–333.
- NICHOLSON, P., & SHAW, I.: *Ancient Egyptian Materials and Technology*, Cambridge (Cambridge University Press) 2000.

- PALLA, F, ET AL: « Essential Oils as Natural Biocides in Conservation of Cultural Heritage», *Molecules* 25, 2020, 730-741.
- REYES-ESTEBANEZ, M., ET AL: «Antimicrobial Engineered Nanoparticles in the Built Cultural Heritage Context and Their Ecotoxicological Impact on Animals and Plants: A Brief Review», *Heritage Sci* 6, 2018, 1–11.
- RICHARDSON, M.J. & WATLING, R.: *Key of Fungi on Dung*, London (British Mycological Society) 1997.
- SEGUIN, P, ET AL: «Successful Treatment of a Brain Abscess due to *Trichoderma longibrachiatum* After Surgical Resection», *Eur, Journal Clin. Microbiol Infect Dis* 14, 1995, 445–448.
- SHALINI, S. & KOTASTHANE A. S.: «Parasitism of *Rhizoctonia Solani* by Strains of *Trichoderma* spp», *EJEAF Che*, vol.6, 2007, 2272-2281.
- SHARMA, P., KUMAR, V. P., RAMESH, R., SARAVANAN, K., DEEP, S., SHARMA, M., MAHESH, S. & DINESH, S.: «Biocontrol Genes from *Trichoderma* Species: A Review», *African Journal of Biotechnology* 10, 2011, 19898-19907.
- STERFINGER, K.: «Fungi: Their Role in Deterioration of Cultural Heritage», *Fungal Biol Rev.* 24, 2010, 47–55.
- STERFINGER, K, ET AL: «Future Directions and Challenges in Biodeterioration Research on Historic Materials and Cultural Properties», *Inter. Biodeterior Biodegrad* 129, 2018, 10–12.
- STERFLINGER, K.: «Temperature and NaCl-Tolerance of Rock-Inhabiting Meristematic Fungi», *Antonie Van Leeuwenhoek* 74, 1998, 271–281.
- STERNBERG, D., & DOVAL, S.: «Cellulase Production and Ammonia Metabolism in *Trichoderma reesei* on High levels of Cellulose», *Biotechnol Bioeng.* 21, 1980, 181–192.
- STEYAERT, J.M., WELD, R.J. & STEWART, A.: «Ambient pH Intrinsically Influences *Trichoderma* Conditions and Colony Morphology», *Fungal Biol* 114, 2010A, 198–208.
- STEYAERT, J.M., WELD, R.J. & STEWART, A.: «Isolate Specific Conditions in *Trichoderma* in Response to Different Nitrogen Sources», *Fungal Biol* 114, 2010B, 179–188.
- TOPPS, J.H. & WAIN, R.L.: « Investigation on Fungicides. III. the Fungi toxicity of 3- and-5-Alkyl Salicylanilide and Pchlonilines», *Annals of Applied Biology* 45, 1957, 506-511.
- TURNAU, K, ET AL: «Microbes of XVI Century Arrases of Krakow Royal Castle», *Microbiol. Res.* 238, 2020, 126485-126492.
- VENERANDA, M, ET AL: «Biodeterioration of Pompeian Mural Paintings: Fungal Colonization Favored by the Presence of Volcanic Material Residues», *Environ Sci Pollut Res* 24, 2017, 19599–19608.
- VITERBO, A, ET AL: «Antifungal Activity of a Novel Endochitinase Gene (chit36) From *Trichoderma harzianum* Rifai TM, FEMS», *Microbiology Letters* 200, 2001, 169–174.
- ZHANG, S, ET AL: « Identification of the Antifungal Activity of *Trichoderma longibrachiatum* T6 and Assessment of Bioactive Substances in Controlling Phytopathogens», *Pestic Biochem. Physiol* 147, 2018, 59–66.
- ZHOU, P, ET AL: «A Trichodermones A–C, Three New Secondary Metabolites from the Solid Culture of an Endophytic Fungal Strain, *Trichoderma atroviride*», *Fitoterapia* 123, 2017, 18–22.
- ZHU, H, ET AL: «Biological Weed Control Using *Trichoderma polysporum* Strain HZ-31», *Crop. Prot* 134, 2020, 105161.